

**Tetrasubstituted copper phthalocyanines : correlation between liquid crystalline properties, films alignment and sensing propertie**

DAKOGLU GULMAZ, Asuman, POLYAKOV, Maxim S., VOLCHEK, Victoria V., TUNCEL KOSTAKOGLU, Sinem, ESENPINAR, Aliye Ash, BASOVA, Tamara V., DURMUS, Mahmut, GUREK, Ayse Gul, AHSEN, Vefa, BANIMUSLEM, Hikmat Adnan and HASSAN, Aseel <<http://orcid.org/0000-0002-7891-8087>>

Available from Sheffield Hallam University Research Archive (SHURA) at:

<http://shura.shu.ac.uk/13811/>

---

This document is the author deposited version. You are advised to consult the publisher's version if you wish to cite from it.


**Published version**

DAKOGLU GULMAZ, Asuman, POLYAKOV, Maxim S., VOLCHEK, Victoria V., TUNCEL KOSTAKOGLU, Sinem, ESENPINAR, Aliye Ash, BASOVA, Tamara V., DURMUS, Mahmut, GUREK, Ayse Gul, AHSEN, Vefa, BANIMUSLEM, Hikmat Adnan and HASSAN, Aseel (2017). Tetrasubstituted copper phthalocyanines : correlation between liquid crystalline properties, films alignment and sensing propertie. *Sensors and Actuators B: Chemical*, 241, 364-375.

---


**Copyright and re-use policy**

See <http://shura.shu.ac.uk/information.html>

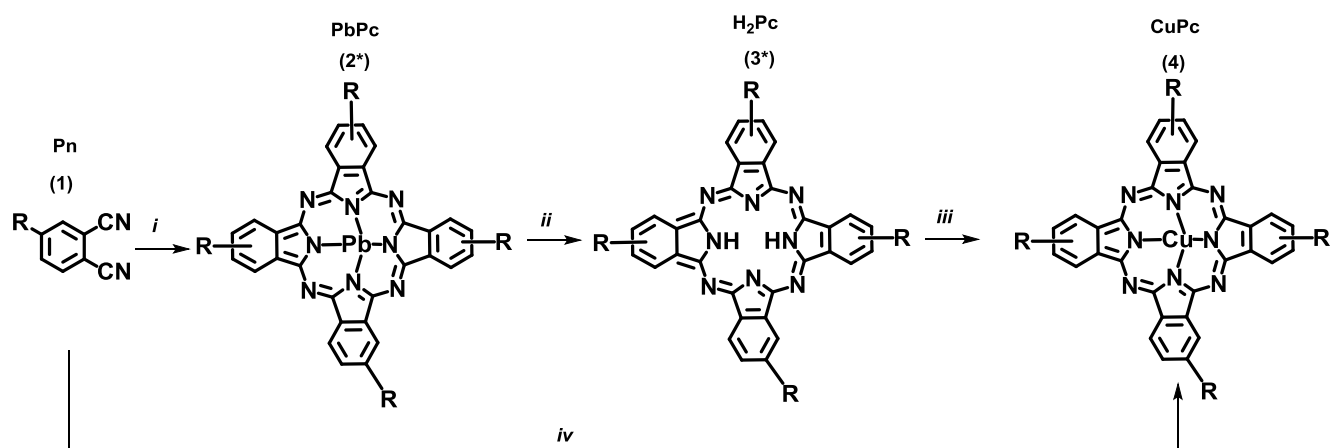


R	Pn (1)	PbPc (2*)	H <sub>2</sub> Pc (3*)	CuPc (4)	Synthetic Route
-OC <sub>8</sub> H <sub>17</sub>	1a	2a	3a	4a	<i>i, ii, iii</i>
-O <sub>16</sub> H <sub>33</sub>	1b	2b	3b	4b	<i>i, ii, iii</i>
-SC <sub>8</sub> H <sub>17</sub>	1c	2c	3c	4c	<i>i, ii, iii</i>
-SC <sub>16</sub> H <sub>33</sub>	1d	2d	3d	4d	<i>i, ii, iii</i>
-O(CH <sub>2</sub> CH <sub>2</sub> O) <sub>3</sub> CH <sub>3</sub>	1e			4e	<i>iv</i>
-S(CH <sub>2</sub> CH <sub>2</sub> O) <sub>3</sub> CH <sub>3</sub>	1f			4f	<i>iv</i>


**Figure 1.** Synthesis of CuPc derivatives, **4a-4c**, **4d** [34], **4e-f** [35]. *i*: anhydrous PbO, solvent-free, 210°C, 5h. *ii*: CH<sub>3</sub>COOH. *iii*: anhydrous CuCl<sub>2</sub>, anhydrous n-hexanol, reflux, 2h. *iv*: anhydrous CuCl<sub>2</sub>, anhydrous n-hexanol, DBU, reflux, 24h. \*PbPc (**2**) and H<sub>2</sub>Pc (**3**) derivatives were not purified but directly used for the synthesis of CuPc derivatives (**4a-d**).

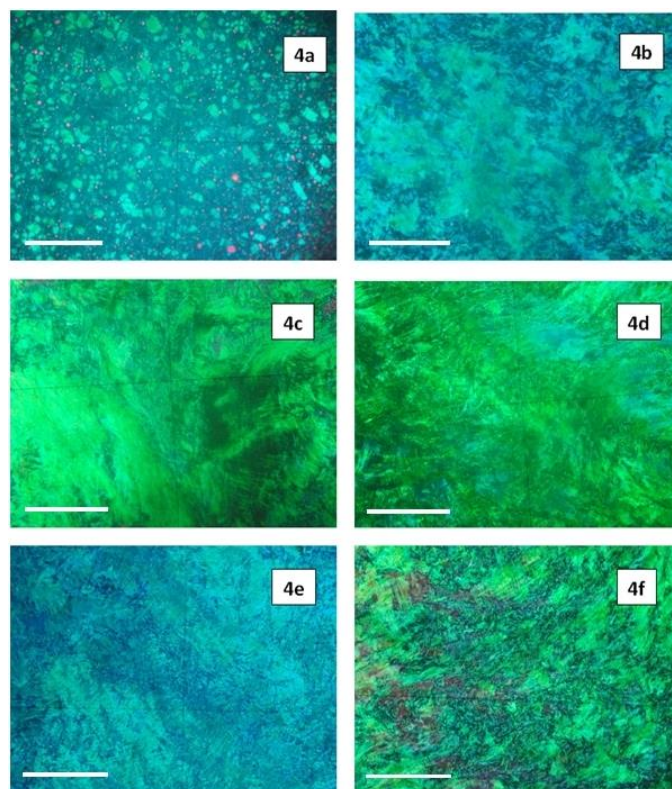


**Figure 2.** POM images of CuPcs (**4a-f**). The scale bar indicates 100 μm.

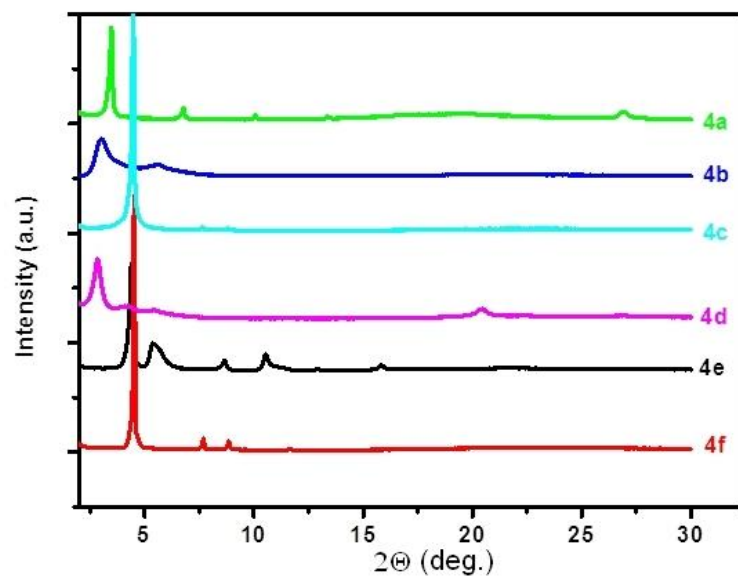


**Figure 3.** XRD patterns of CuPc derivatives (**4a-f**) measured at room temperature.

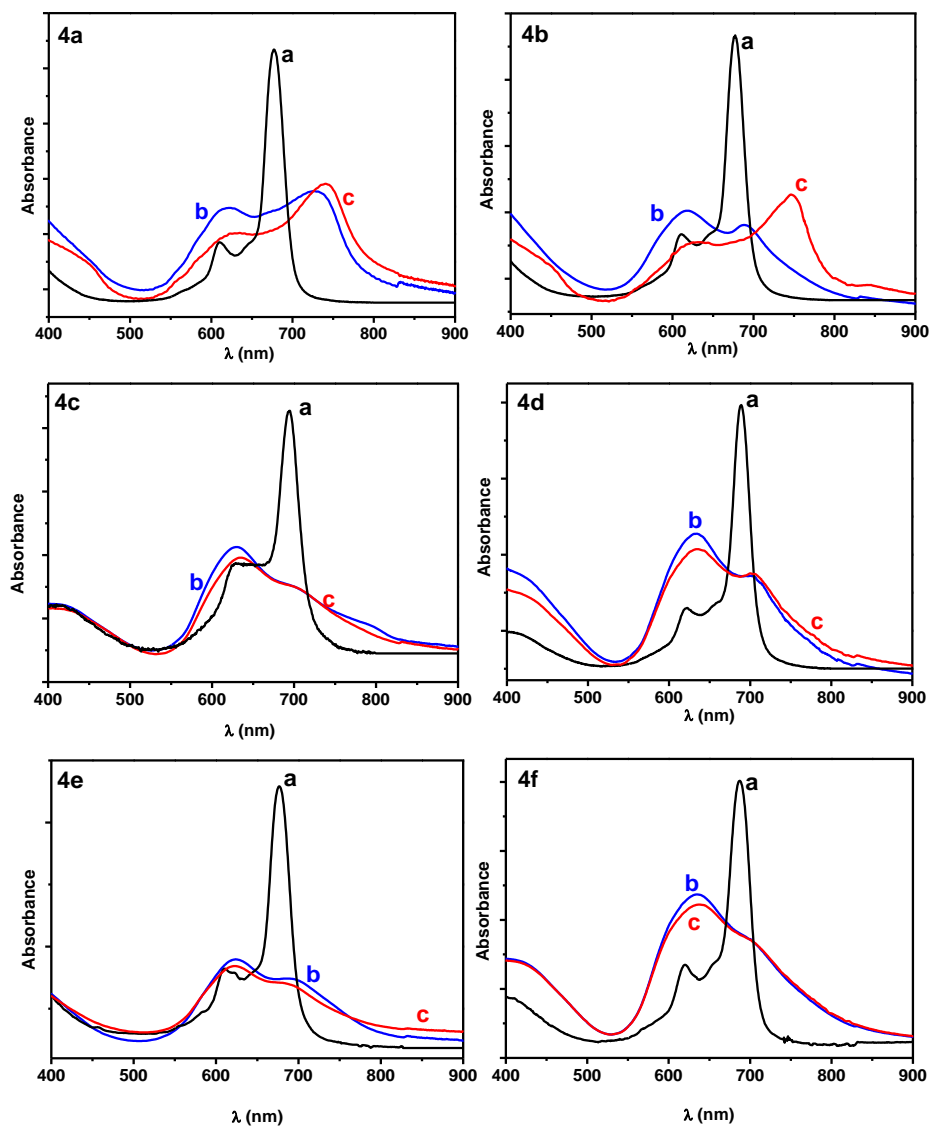


**Figure 4.** Optical absorption spectra of CuPc (**4a-f**): solutions in dichloromethane (a), as-deposited films (b), films after heat treatment (c).

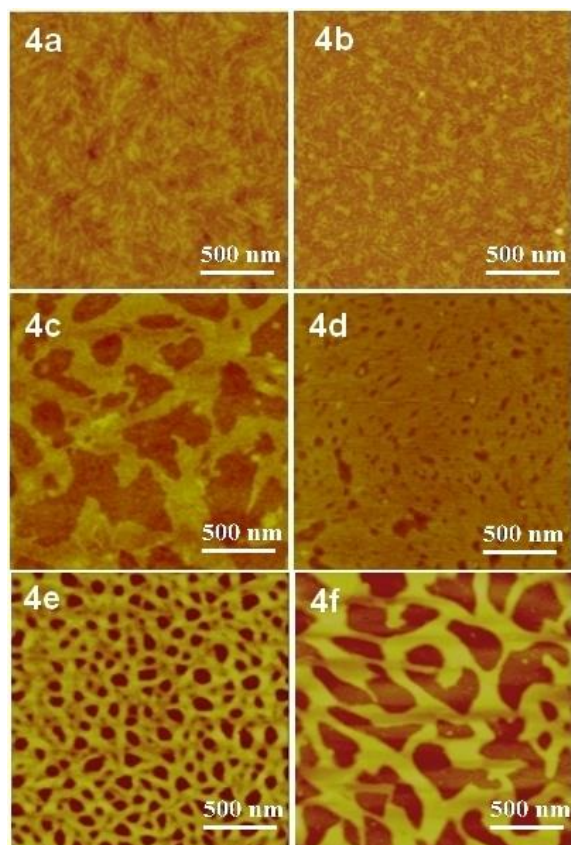

**Figure 5.** AFM images of the films of CuPcs (**4a-f**).

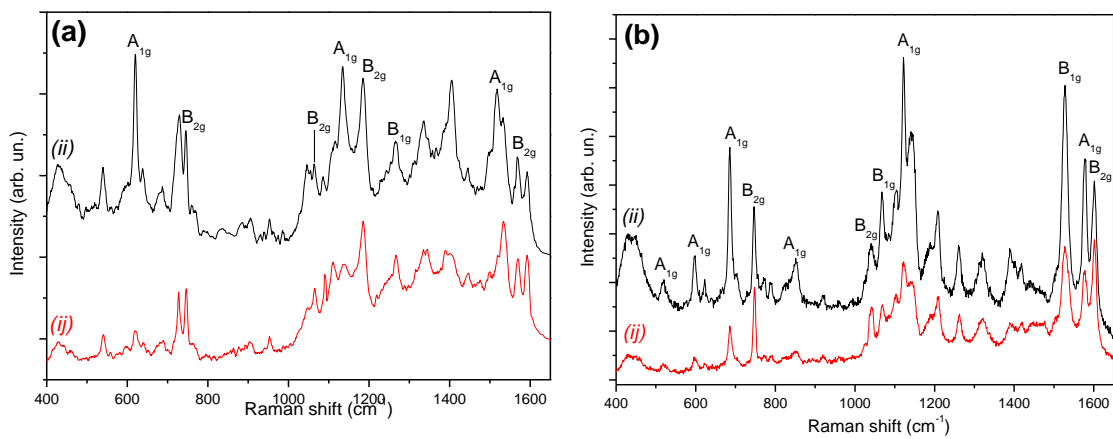


**Figure 6.** Polarized Raman spectra of **4b** (a) and **4d** (b) films on glass substrates after heat treatment.

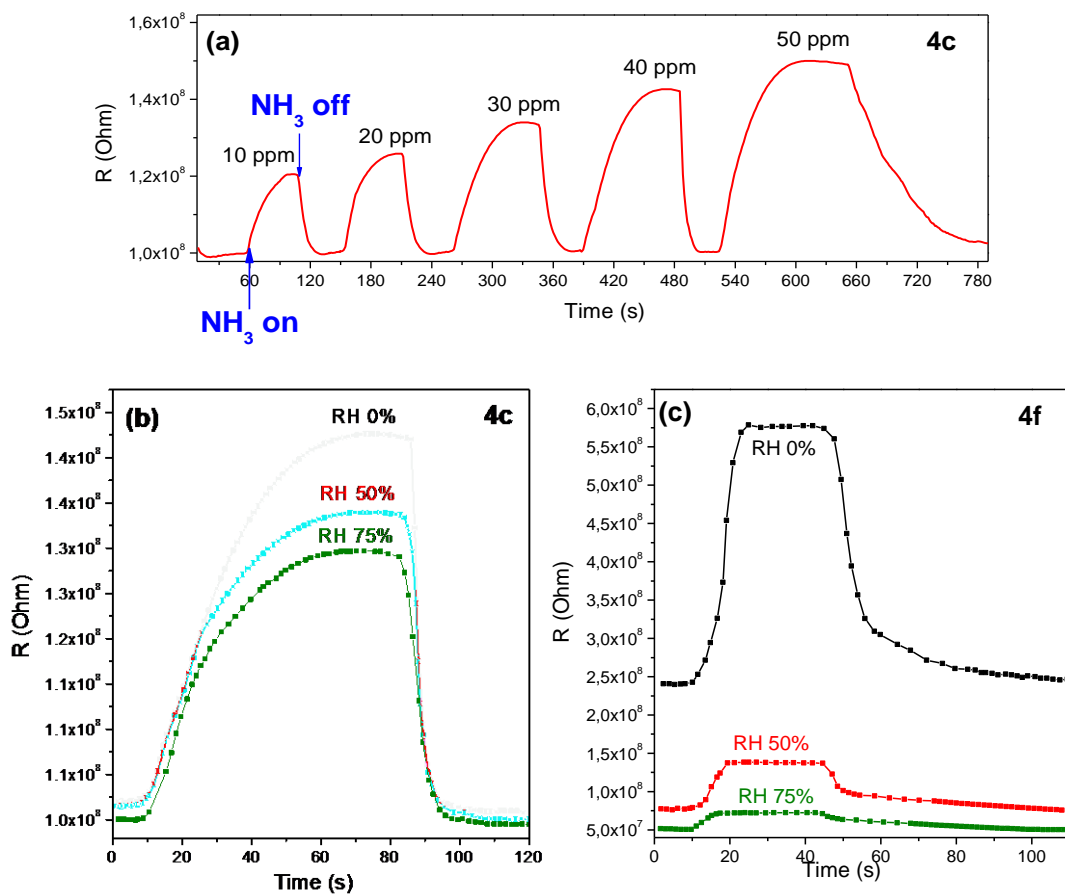


**Figure 7.** Response curves of the film of **4c** to ammonia vapours at concentrations of 10-50 ppm (a) measured at 50%. Response curves of the films of **4c** (b) and **4f** (c) to ammonia vapours (30 ppm) measured at different relative humidities.



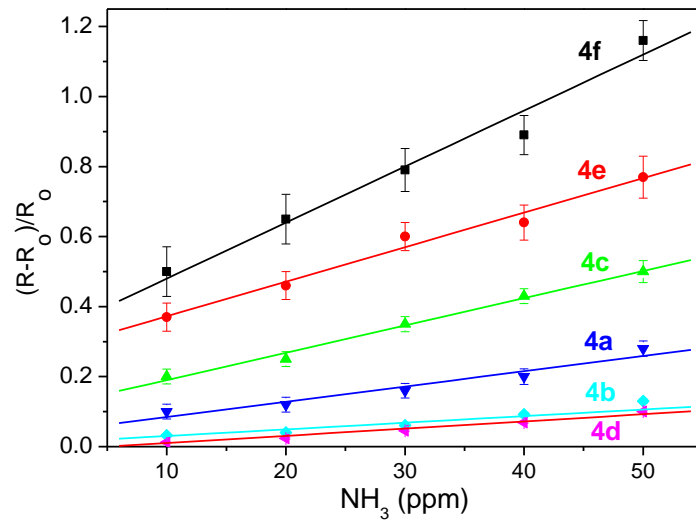

**Figure 8.** Normalized sensor response vs  $\text{NH}_3$  concentration, measured at RH 50%.

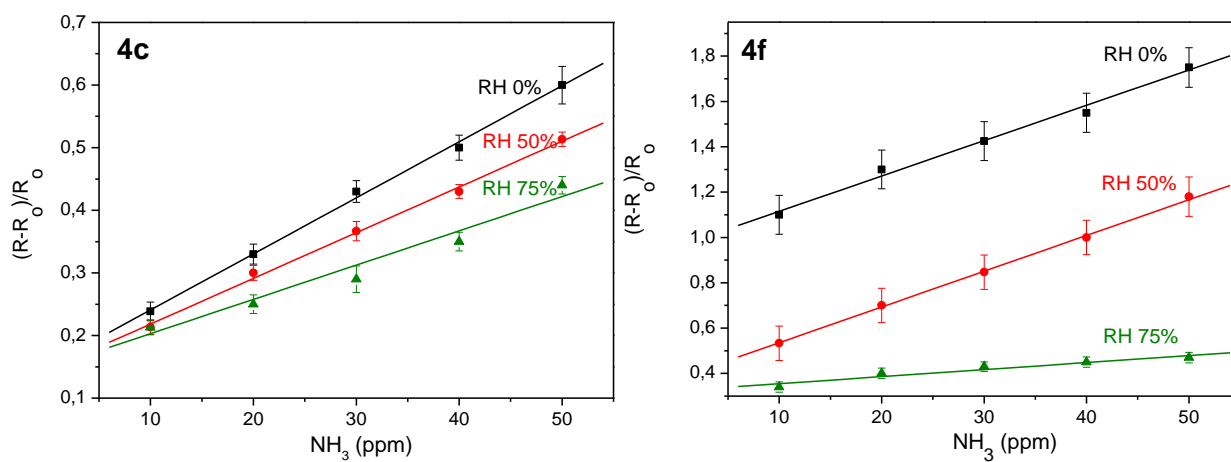

**Figure 9.** Normalized sensor response of **4c** and **4f** films vs  $\text{NH}_3$  concentration, measured at RH 0, 50 and 75%.