

Temperature dependent, large electromechanical strain in Nd-doped BiFeO₃-BaTiO₃ lead-free ceramics

WANG, Dawei, KHESRO, Amir, MURAKAMI, S, FETEIRA, Antonio <<http://orcid.org/0000-0001-8151-7009>>, ZHAO, Quanliang and REANEY, Ian M.

Available from Sheffield Hallam University Research Archive (SHURA) at:

<http://shura.shu.ac.uk/14516/>

This document is the author deposited version. You are advised to consult the publisher's version if you wish to cite from it.

Published version

WANG, Dawei, KHESRO, Amir, MURAKAMI, S, FETEIRA, Antonio, ZHAO, Quanliang and REANEY, Ian M. (2016). Temperature dependent, large electromechanical strain in Nd-doped BiFeO₃-BaTiO₃ lead-free ceramics. *Journal of the European Ceramic Society*.

Copyright and re-use policy

See <http://shura.shu.ac.uk/information.html>

Contents lists available at www.sciencedirect.com

Journal of the European Ceramic Society

journal homepage: www.elsevier.com/locate/jeurceramsoc

Short communication

Temperature dependent, large electromechanical strain in Nd-doped BiFeO₃-BaTiO₃ lead-free ceramicsDawei Wang^{a,c}, Amir Khesro^a, Shunsuke Murakami^a, Antonio Feteira^b, Quanliang Zhao^c, Ian M. Reaney^{a,*}^a Department of Materials Science and Engineering, University of Sheffield, Sheffield S1 3JD, UK^b Christian Doppler Laboratory for Advanced Ferroic Oxides, Sheffield Hallam University, Sheffield S1 1WB, UK^c Department of Materials Science and Engineering, North China University of Technology, Beijing 100144, China

ARTICLE INFO

Article history:

Received 6 October 2016
Received in revised form 21 October 2016
Accepted 22 October 2016
Available online xxx

Keywords:

BiFeO₃-BaTiO₃
Ferroelectrics
Relaxors
Piezoelectricity
Strain

ABSTRACT

Lead-free piezoceramics with the composition 0.7(Bi_{1-x}Nd_x)FeO₃-0.3BaTiO₃+0.1 wt% MnO₂ (BNxF-BT) were prepared using a conventional solid state route. X-ray diffraction and temperature dependent permittivity measurements indicated a transition from a composition lying at a morphotropic phase boundary (MPB) to a pseudocubic phase as a function of Nd concentration. The highest maximum strain ($S_{\max} \sim 0.2\%$ at 60 kV/cm) and effective piezoelectric coefficient ($d_{33}^* = 333$ pm/V) were obtained at room temperature for the composition BN0.02F-BT. The decrease in remanent polarization (P_r) and Berlincourt d_{33} with increase in Nd concentration can be attributed to the coexistence of ferroelectric and relaxor phases. *In-situ* polarisation and strain measurements revealed an increase in P_r and d_{33}^* with temperature and a reduction in the coercive field E_c . Presumably this behavior is due to a combination of thermally activated domain wall motion and lowering of the activation energy for a field induced relaxor-ferroelectric transition, as the Curie maximum is approached.

© 2016 Published by Elsevier Ltd.

1. Introduction

Bismuth ferrite (BiFeO₃, BF) is a multiferroic material with a rhombohedrally distorted perovskite structure (space group $R3c$) at room temperature (RT). BF is popular for the rare coexistence of the antiferromagnetic and ferroelectric order with a Neel temperature (T_N) of ~ 643 K and a Curie temperature (T_C) of ~ 1103 K [1,2]. The latter property is of interest for high temperature piezoelectric applications. Furthermore, BF is environmentally-friendly in comparison to lead containing piezoelectric materials and can therefore meet the regulations on protection of environment and human health [2]. However, BF exists only in a narrow temperature range, making the synthesis of single phase BF without secondary phases such as Bi₂Fe₄O₉ and Bi₂₅FeO₄₀ a difficult task by conventional methods [2–4]. Furthermore, BF ceramics usually exhibit high electrical leakage because of the reduction of Fe ions from Fe³⁺ to Fe²⁺ during sintering and the formation of oxygen vacancies for charge compensation [5,6], leading to the difficulties in obtaining saturated polarization hysteresis loop and piezoelectric response.

Therefore, to reduce the leakage current, inhibit the formation of secondary phases and improve properties, extensive studies have been carried out, including the substitution of various ions for Bi³⁺/Fe³⁺ in BF [7–13] and the formation of BF-based solid solutions with other ABO₃ type perovskites (e.g. BaTiO₃, Ba(Zr,Ti)O₃ and Bi_{0.5}K_{0.5}TiO₃) [14–19]. It should be noted that multiferroic BiFeO₃-BaTiO₃ (BF-BT) solid solution has been frequently studied and proved to be a high- T_C lead-free piezoelectric ceramic [14–17]. However, most of these investigations on BF-BT focus on the properties at RT and rarely provide the temperature dependence of properties, which is critical for practical applications. In addition, it is reported that the substitution of rare earth ions for Bi³⁺ in BF can enhance their piezoelectricity and ferroelectricity [7–13]. Consequently, in this work, Nd-doped BF-BT lead-free ceramics were prepared by a conventional sintering technique and the composition and temperature dependence of the ferroelectricity and electric-field induced strain were investigated.

2. Experimental procedure

The BF-based ceramics with compositions of 0.7(Bi_{1-x}Nd_x)FeO₃-0.3BaTiO₃+0.1 wt% MnO₂ (BNxF-BT, x=0, 0.005, 0.01, 0.02, 0.05) were prepared using a conventional solid state reaction. A small

* Corresponding author.

E-mail address: i.m.reaney@sheffield.ac.uk (I.M. Reaney).

amount of MnO_2 was added to increase the resistivity of BF-BT ceramics, which is commonly used in previous reports [15–19]. Raw materials, including Bi_2O_3 (99.9%, Sigma-Aldrich), Fe_2O_3 (99.5%, Sigma-Aldrich), Nd_2O_3 (99.5%, Sigma-Aldrich), TiO_2 (99.9%, Sigma-Aldrich), and BaCO_3 (99%, Sigma-Aldrich) were batched stoichiometrically according to the nominal compositions and ball-milled in isopropanol for 24 h. The dried mixed powders were calcined at 700 to 800 °C for 2 h to synthesize the compound and then ball milled in isopropanol with MnO_2 (99%, Sigma-Aldrich) for 12 h. The calcined powders were mixed with a polyvinyl alcohol (PVA) binder solution, granulated and pressed into pellets with a diameter of 10 mm. Following binder burnout at 550 °C, the pellets were sintered in a sealed crucible at 1010–1040 °C for 2 h.

The density of the sintered samples was measured using Archimedes method. The relative density of all studied samples was higher than 95%. The phase structure of the sintered samples was studied using a Bruker D2 Phaser X-ray powder diffraction (XRD). For electrical tests, sintered samples were electroded using fired-on silver paste, followed by the samples being poled in silicon oil at 100–120 °C with an applied electric field of 40–60 kV/cm. Piezoelectric coefficient (d_{33}) was measured using a Piezotest PM300 d_{33} meter. Polarization hysteresis and strain-electric field behaviour were determined using a modified Sawyer-Tower circuit driven by a lock-in amplifier (Model SR830, Stanford Research System, Sunnyvale, CA) at a frequency of 1 Hz from RT to 150 °C. The temperature dependent of dielectric property from RT to 550 °C was carried out using an Agilent 4184A multi-frequency precision LCR meter.

3. Results and discussion

The RT XRD patterns of $\text{BN}_x\text{F-BT}$ in the 2θ range of 20°–70° are shown in Fig. 1(a). All peaks could be attributed to a single perovskite phase, indicating that a stable solid solution was formed in the studied range. Diffraction peaks shifted to a higher diffraction angle with increasing Nd concentration, consistent with the smaller relative ionic radius of Nd^{3+} ions compared to that of Bi^{3+} ions in the matrix composition [11,12]. Splitting of (012)/(110) diffraction peak at $\sim 2\theta = 32^\circ$ was used to determine the likely symmetry of compositions. From the expanded XRD patterns (Fig. 1a), phase coexistence in the BF-BT matrix is apparent at RT as shown by the broad multiple peaks, which have been reported to indicate a morphotropic phase boundary (MPB) [14,15,20]. As Nd concentration increased, a pseudocubic phase followed by the appearance of one merged peak as observed in refs [14,15,20].

The temperature dependence of dielectric permittivity (ϵ_r) and loss ($\tan \delta$) for $\text{BN}_x\text{F-BT}$ at 100 kHz is given in Fig. 1(b). With increasing Nd concentration, the T_C /Curie maximum (T_m) decreased monotonously (inset of Fig. 1b), presumably due to disruption of polar coupling by the substitution of the less polarisable Nd for Bi [20,21]. The decrease in polar coupling also manifested itself by relaxor-like characteristics, with the appearance of broad frequency-dependent dielectric peaks. Despite these changes, $\tan \delta$ remained low below 400 °C, but then increased sharply (Fig. 1b), indicating an increase in dc conductivity at high temperature.

The high electric field bipolar polarization hysteresis (P-E) and unipolar strain (S-E) loops for $\text{BN}_x\text{F-BT}$ are shown in Fig. 2(a and b), from which the remanent polarization (P_r), coercive field (E_c) and average electric field induced maximum strain (S_{\max}) as a function of Nd content can be obtained, Fig. 2(c and d). The normalized strain coefficient d_{33}^* , representing the average strain per unit of electric field, is calculated by, $d_{33}^* = S_{\max}/E_{\max}$, where E_{\max} is the maximum electric field value. The BF-BT sample possessed a typical saturated hysteresis loops (Fig. 2a), indicating high resistivity and good sintering behaviour of the fabricated samples. With increasing

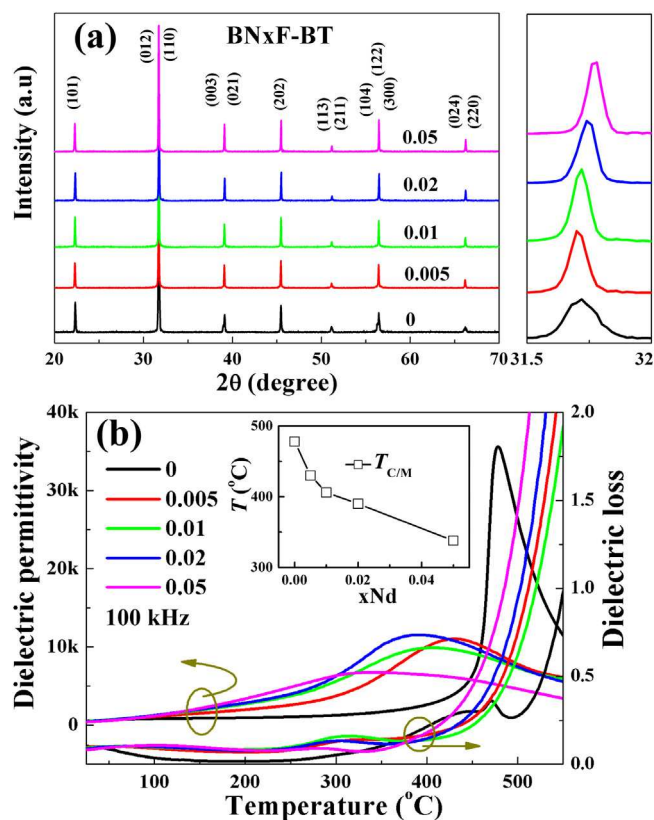


Fig. 1. (a) RT XRD patterns of $\text{BN}_x\text{F-BT}$ and (b) Temperature dependence of ϵ_r and $\tan \delta$ at 100 kHz for $\text{BN}_x\text{F-BT}$, inset shows $T_{C/M}$ as a function of Nd concentration.

Table 1

Comparison of temperature dependence of d_{33}^* for various piezoelectric ceramics (PZT, $\text{Pb}(\text{Zr,Ti})\text{O}_3$; BNT-BT-BKT, $\text{Bi}_{0.5}\text{Na}_{0.5}\text{TiO}_3$ - BaTiO_3 - $\text{Bi}_{0.5}\text{K}_{0.5}\text{TiO}_3$).

Material	Temperature range	Increase in d_{33}^*	Reference
PZT-4	RT–160 °C	15%	23
PZT-5H	RT–80 °C	>40%	24
BNT-BT-BKT	RT–100 °C	273%	25
BF	RT–262 °C	258%	22
BF-0.3BT	RT–150 °C	42%	This work
BN0.02F-0.3BT	RT–150 °C	117%	This work

Nd concentration, P-E loops became slim and unsaturated (Fig. 2a), with P_r , E_c and d_{33}^* continuously decreasing (Fig. 2c), consistent with the broad permittivity maximum (Fig. 1b) and indicative of relaxor-like behaviour. The highest value of $P_r \sim 36.6 \mu\text{C}/\text{cm}^2$, $E_c \sim 33.6 \text{ kV}/\text{cm}$ and $d_{33}^* \sim 190 \text{ pC}/\text{N}$ was achieved for the BF-BT matrix without Nd doping due to the presence of an MPB (Fig. 1a) [14,15]. At the same time, the S_{\max} and d_{33}^* values increased significantly with increasing Nd concentration, reaching a maximum of 0.2% and 333 pm/V at $x = 0.02$, above which it reduced, Fig. 2(d). The enhancement of the S_{\max} and d_{33}^* in BN0.02F-BT is attributed to the crossover from normal to relaxor ferroelectric behaviour.

The *in-situ* temperature dependence of bipolar P-E and unipolar S-E loops for two compositions are shown in Fig. 3(a and b), from which the P_r , E_c and d_{33}^* as a function of temperature were obtained, Fig. 3(c). As temperature increased, the P-E loops for each composition became saturated and slim (Fig. 3a), which implies that higher temperature effectively promotes the movement of domain walls and/or facilitates an easier field induced transition from a relaxor to a ferroelectric state, resulting in higher P_r , d_{33}^* and lower E_c as shown in Fig. 3(c). Similar behaviour has also been found in other lead-based/lead-free ceramics as given in Table 1 [22–25]. For example, the increase in d_{33}^* for pure BF-BT is $\sim 42\%$,

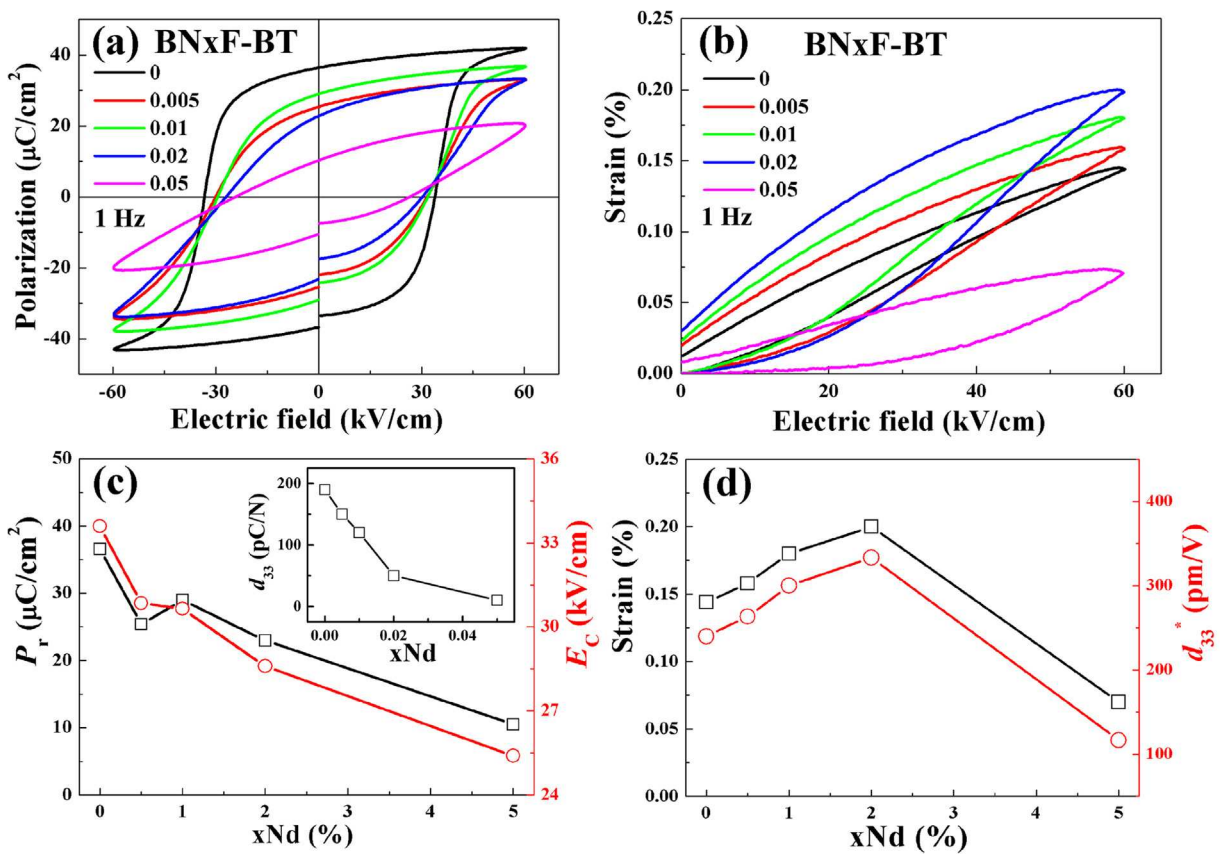


Fig. 2. High electric field (a) bipolar polarization hysteresis and (b) unipolar strain loops for BNxF-BT; (c) P_r and E_c as a function of Nd concentration, inset shows d_{33} as a function of Nd concentration; (d) S_{max} and d_{33}^* as a function of Nd concentration.

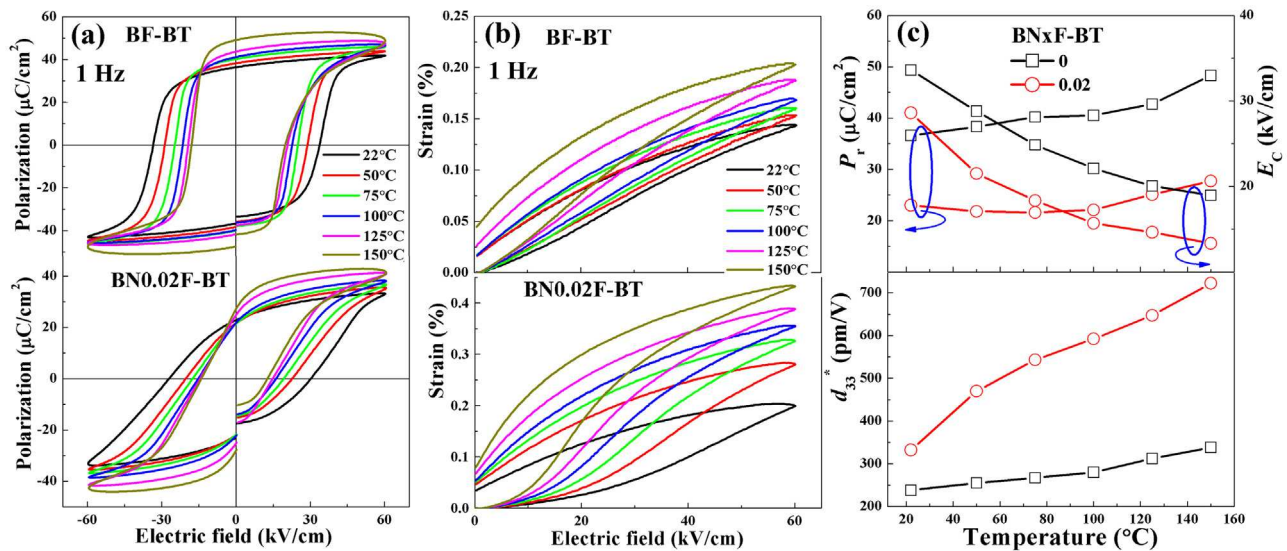


Fig. 3. The *in-situ* temperature dependence of high electric field (a) bipolar polarization hysteresis and (b) unipolar strain loops for BF-BT and BN0.02F-BT; (c) P_r , E_c and d_{33}^* as a function of temperature.

lower than that of BN0.02F-BT (~117%). However, detailed knowledge of the domain morphology and its field dependence is required to fully appreciate the relative contributions of domain wall motion versus field induced transitions to d_{33}^* in BN0.02F-BT ceramics.

4. Conclusion

In this work, BNxF-BT lead-free piezoelectric ceramics were successfully prepared using a conventional solid state route. With increasing Nd concentration, the phase assemblage of BNxF-BT gradually transformed from an MPB to a pseudocubic phase. The

highest $P_r \sim 36.6 \mu\text{C}/\text{cm}^2$, $E_C \sim 33.6 \text{ kV}/\text{cm}$ and $d_{33} = 190 \text{ pC}/\text{N}$ were obtained for the pure BF-BT due the presence of the MPB. However, the optimum $S_{\text{max}} \sim 0.2\%$ and $d_{33}^* = 333 \text{ pm}/\text{V}$ were achieved at RT for the composition doped with 0.02 mol% Nd, attributed to the coexistence of ferroelectric and relaxor phases. In addition, the *in-situ* temperature dependence of ferroelectric and strain behavior indicated that the P-E loops became more and more saturated and slim with increasing temperature, resulting in higher P_r , d_{33}^* and lower E_C .

Acknowledgements

We thanks Prof. Susan Trolier-McKinstry and Prof. Clive Randall from Materials Research Institute of Pennsylvania State University for the help and discussion. We acknowledge the Sustainability and Substitution of Functional Materials and Devices EPSRC (EP/L017563/1) and the National Natural Science Foundation of China (51402005) for funding and supporting this work. A.K. acknowledges Abdul Wali Khan University Mardan for Ph.D. studentship.

References

- [1] R. Ramesh, A.S. Nicola, Multiferroics: progress and prospects in thin films, *Nat. Mater.* 6 (2007) 21–29.
- [2] T. Rojac, A. Bencan, B. Malic, G. Tutuncu, J.L. Jones, J.E. Daniels, D. Damjanovic, BiFeO₃ ceramics: processing, electrical, and electromechanical properties, *J. Am. Ceram. Soc.* 97 (2014) 1993–2011.
- [3] I. Sosnowska, T. Peterlinneumaier, E. Steichele, Spiral magnetic ordering in bismuth ferrite, *J. Phys. C: Solid State Phys.* 15 (1982) 4835–4846.
- [4] R. Palai, R.S. Katiyar, H. Schmid, P. Tissot, S.J. Clark, J. Robertson, S. Redfern, G. Catalan, J.F. Scott, Beta phase and gamma-beta metal-insulator transition in multiferroic BiFeO₃, *Phys. Rev. B* 77 (2008) 014110.
- [5] A.K. Pradhan, K. Zhang, D. Hunter, J.B. Dadson, G.B. Loiutts, P. Bhattacharya, R. Katiyar, J. Zhang, D.J. Sellmyer, U.N. Roy, Y. Cui, A. Burger, Magnetic and electrical properties of single-phase multiferroic BiFeO₃, *J. Appl. Phys.* 97 (2005) 093903.
- [6] S.K. Pradhan, B.K. Roul, Improvement of multiferroic and leakage property in monophasic BiFeO₃, *Phys. B* 406 (2011) 3313–3317.
- [7] K. Kalantari, I. Sterianou, S. Karimi, M.C. Ferrarelli, S. Miao, D.C. Sinclair, I.M. Reaney, Ti-doping to reduce conductivity in Bi_{0.85}Nd_{0.15}FeO₃ ceramics, *Adv. Funct. Mater.* 21 (2011) 3737–3743.
- [8] A. Khesro, R. Boston, I. Sterianou, D.C. Sinclair, I.M. Reaney, Phase transitions, domain structure, and pseudosymmetry in La- and Ti-doped BiFeO₃, *J. Appl. Phys.* 119 (2016) 054101.
- [9] D. Kan, L. Palova, V. Anbusathaiah, C.J. Cheng, S. Fujino, V. Nagarajan, K.M. Rabe, I. Takeuchi, Universal behavior and electric-field-induced structural transition in rare-earth-substituted BiFeO₃, *Adv. Funct. Mater.* 20 (2010) 1108–1115.
- [10] T. Zheng, J. Wu, Effects of site engineering and doped element types on piezoelectric and dielectric properties of bismuth ferrite lead-free ceramics, *J. Mater. Chem. C* 3 (2015) 11326–11334.
- [11] D. Wang, M. Wang, F. Liu, Y. Cui, Q. Zhao, H. Sun, H. Jin, M. Cao, Sol-gel synthesis of Nd-doped BiFeO₃ multiferroic and its characterization, *Ceram. Int.* 41 (2015) 8768–8772.
- [12] Y. Li, W. Cao, J. Yuan, D. Wang, M. Cao, Nd doping of bismuth ferrite to tune electromagnetic properties and increase microwave absorption by magnetic–dielectric synergy, *J. Mater. Chem. C* 3 (2015) 9276–9282.
- [13] Y. Li, M. Cao, D. Wang, J. Yuan, High-efficiency and dynamic stable electromagnetic wave attenuation for La doped bismuth ferrite at elevated temperature and gigahertz frequency, *RSC Adv.* 5 (2015) 77184–77191.
- [14] M.H. Lee, D.J. Kim, J.S. Park, S.W. Kim, T.K. Song, M.H. Kim, W.J. Kim, D. Do, I.K. Jeong, High-performance lead-free piezoceramics with high curie temperatures, *Adv. Mater.* 27 (2015) 6976–6982.
- [15] S.O. Leontsev, R.E. Eitel, Dielectric and piezoelectric properties in Mn-modified (1-x)BiFeO₃-xBaTiO₃ ceramics, *J. Am. Ceram. Soc.* 92 (2009) 2957–2961.
- [16] Y. Guo, P. Xiao, R. Wen, Y. Wan, Q. Zheng, D. Shi, K.H. Lam, M. Liu, D. Lin, Critical roles of Mn-ions in enhancing the insulation, piezoelectricity and multiferroicity of BiFeO₃-based lead-free high temperature ceramics, *J. Mater. Chem. C* 3 (2015) 5811–5824.
- [17] H. Yang, C. Zhou, X. Liu, Q. Zhou, G. Chen, W. Li, H. Wang, Piezoelectric properties and temperature stabilities of Mn- and Cu-modified BiFeO₃-BaTiO₃ high temperature ceramics, *J. Eur. Ceram. Soc.* 33 (2013) 1177–1183.
- [18] J. Chen, J. Cheng, High electric-induced strain and temperature-dependent piezoelectric properties of 0.75BF-0.25BZT lead-free ceramics, *J. Am. Ceram. Soc.* 99 (2016) 536–542.
- [19] J. Bennett, A.J. Bell, T.J. Stevenson, R.I. Smith, I. Sterianou, I.M. Reaney, T.P. Comyn, Multiferroic properties of BiFeO₃-(K_{0.5}Bi_{0.5})TiO₃ ceramics, *Mater. Lett.* 94 (2013) 172–175.
- [20] Q. Zheng, L. Luo, K.H. Lam, N. Jiang, Y. Guo, D. Lin, Enhanced ferroelectricity, piezoelectricity, and ferromagnetism in Nd-modified BiFeO₃-BaTiO₃ lead-free ceramics, *J. Appl. Phys.* 116 (2014) 184101.
- [21] Q. Zhou, C. Zhou, H. Yang, G. Chen, W. Li, H. Wang, Dielectric ferroelectric, and piezoelectric properties of Bi(Ni_{1/2}Ti_{1/2})O₃-modified BiFeO₃-BaTiO₃ ceramics with high curie temperature, *J. Am. Ceram. Soc.* 95 (2012) 3889–3893.
- [22] T. Rojac, M. Makarovic, J. Walker, H. Ursic, D. Damjanovic, T. Ko, Piezoelectric response of BiFeO₃ ceramics at elevated temperatures, *Appl. Phys. Lett.* 109 (2016) 042904.
- [23] Y. Saito, H. Takao, T. Tani, T. Nonoyama, K. Takatori, T. Homma, T. Nagaya, M. Nakamura, Lead-free piezoceramics, *Nature* 432 (2004) 84–87.
- [24] D. Wang, Y. Fotinich, G.P. Carman, Influence of temperature on the electromechanical and fatigue behavior of piezoelectric ceramics, *J. Appl. Phys.* 83 (1998) 5342–5350.
- [25] S.T. Zhang, B. Yang, W. Cao, The temperature-dependent electrical properties of Bi_{0.5}Na_{0.5}TiO₃-BaTiO₃-Bi_{0.5}K_{0.5}TiO₃ near the morphotropic phase boundary, *Acta Mater.* 60 (2012) 469–475.