

Temperature-dependent micromagnetic model of the antiferromagnet Mn₂Au: A multiscale approach

HIRST, Joel <<http://orcid.org/0000-0001-6041-0106>>, ATXITIA, Unai, RUTA, Sergiu, JACKSON, Jerome, PETIT, Leon and OSTLER, Thomas <<http://orcid.org/0000-0002-1328-1839>>

Available from Sheffield Hallam University Research Archive (SHURA) at:

<https://shura.shu.ac.uk/30728/>

This document is the Published Version [VoR]

Citation:

HIRST, Joel, ATXITIA, Unai, RUTA, Sergiu, JACKSON, Jerome, PETIT, Leon and OSTLER, Thomas (2022). Temperature-dependent micromagnetic model of the antiferromagnet Mn₂Au: A multiscale approach. *Physical Review B*, 106 (9). [Article]

Copyright and re-use policy

See <http://shura.shu.ac.uk/information.html>

Temperature-dependent micromagnetic model of the antiferromagnet Mn_2Au : A multiscale approach

Joel Hirst¹,² Unai Atxitia,^{2,3} Sergiu Ruta,¹ Jerome Jackson⁴, Leon Petit⁴, and Thomas Ostler^{5,1,6}

¹Materials & Engineering Research Institute, Sheffield Hallam University, Sheffield S1 1WB, United Kingdom

²Dahlem Center for Complex Quantum Systems and Fachbereich Physik, Freie Universität Berlin, 14195 Berlin, Germany

³Instituto de Ciencia de Materiales de Madrid, CSIC, Cantoblanco, 28049 Madrid, Spain

⁴Scientific Computing Department, STFC Daresbury Laboratory, Warrington WA4 4AD, United Kingdom

⁵Department of Physics & Mathematics, University of Hull, Hull HU6 7RX, United Kingdom

⁶Department of Engineering and Mathematics, Sheffield Hallam University, Sheffield S1 1WB, United Kingdom



(Received 17 June 2022; revised 16 August 2022; accepted 19 August 2022; published 2 September 2022)

Antiferromagnets (AFMs) are strong candidates for the future spintronic and memory applications largely because of their inherently fast dynamics and lack of stray fields, with Mn_2Au being one of the most promising. For the numerical modeling of magnetic material properties, it is common to use *ab initio* methods, atomistic models, and micromagnetics. However, each method alone describes the physics within certain limits. Multiscale methods bridging the gap between these three approaches have been already proposed for ferromagnetic materials. Here we present a complete multiscale model of the AFM Mn_2Au as an exemplar material, starting with results from *ab initio* methods going via atomistic spin dynamics (ASD) to an AFM Landau-Lifshitz-Bloch (AFM-LLB) model. First, bulk Mn_2Au is modelled using a classical spin Hamiltonian constructed based on earlier first-principles calculations. Second, this spin model is used in the stochastic Landau-Lifshitz-Gilbert to calculate temperature-dependent equilibrium properties, such as magnetization and magnetic susceptibilities. Third, the temperature-dependent micromagnetic parameters are used in the AFM-LLB. We validate our approach by comparing the ASD and AFM-LLB models for three paradigmatic cases: (i) damped magnetic oscillations, (ii) magnetization dynamics following a heat pulse resembling pump-probe experiments, and (iii) magnetic domain wall motion under thermal gradients.

DOI: [10.1103/PhysRevB.106.094402](https://doi.org/10.1103/PhysRevB.106.094402)

I. INTRODUCTION

The interest in antiferromagnetic (AFM) materials has increased in recent years for several reasons. From fundamental questions regarding the effects of atomic-scale spin interactions on the macroscale magnetic configurations [1–4], to contenders for driving future technologies of smaller, faster, and more energy efficient devices [5–10]. Possible applications are in the fields of terahertz (THz) science, ultrafast spin dynamics and spin-caloritronics – combined spin transport and heat.

AFMs are robust against strong external magnetic fields and have intrinsically fast THz magnetization dynamics compared to the (gigahertz) GHz dynamics found in ferromagnets. It has been known since the late 1940s that the resonant modes of certain AFMs can reach the THz range [11,12]. This frequency enhancement in AFMs emerges at the macroscale from the interplay of the magnetic anisotropy and the atomic-scale antiferromagnetic spin exchange interaction. If antiferromagnets are to be used in THz emitters and spintronic devices [13–16], it becomes essential to accurately calculate, from first-principles, the nature and values of the anisotropy and exchange interactions between spins. Microscopic interactions also play a key role in the field of ultrafast spin dynamics [17]. Experiments have demonstrated an

ultrafast and more energy efficient magnetic order quenching in AFM than in FMs [18]. Further understanding and control of the ultrafast spin dynamics in AFMs requires not only accurate determination of the exchange interactions, but also how the magnetic system reacts to an ultrafast load of heat from femtosecond laser pulses.

Metallic AFMs are convenient for all of those aforementioned applications. For instance, the antiferromagnets CuMnAs and Mn_2Au have been proposed [19–24] for several device applications because their magnetic state can be controlled via electric currents, and they can be read out via their magnetoresistive properties [25,26]. They have relatively high critical temperature with experimental measurements placing the Néel temperature of Mn_2Au between 1300 and 1600 K [27] and around 480 K for CuMnAs [28], making them ideal for memory and spintronics applications. While initial studies focused on CuMnAs rather than Mn_2Au , it has been demonstrated that the Joule heating created by electric currents puts the system too close to the critical temperature, so that undesired thermal fluctuations strongly influence the dynamics. In this regard, the much higher critical temperature of Mn_2Au is preferred.

Established approaches to calculate the magnetic properties include *ab initio* methods for the electronic structure at the atomic scale and generally at zero temperature [29–33],

atomistic spin models coupled to a heat-bath for the calculation of thermal properties at the nanoscale [34–36], and micromagnetics for the calculation of the magnetic distribution at the micrometer scale [37–39]. In conventional micromagnetism, the magnetization vector is treated as a continuous vector field where the anisotropy and exchange interactions are coarse grained over distances of several unit cells, and information on the interactions between the individual atomic sites is lost. The Gibbs free energy is formulated on the assumption that the magnetization length remains constant and thus limits micromagnetics to low and constant temperature. *Ab initio* methods and atomistic spin models are able to naturally describe AFMs as they capture the strong variations in the spin orientation on the atomic scale. While micromagnetic modeling of AFMs remains a challenge, ferromagnetic micromagnetic models based on the Landau-Lifshitz-Gilbert (LLG) equation are now well established and used extensively in fundamental and device research. Several codes are available with a plethora of features and are implemented on various high performance computing platforms [37,38,40]. These micromagnetic models are particularly useful when attempting to model scenarios in which the dynamics occur across μm distances and where high frequency spinwaves do not contribute to the dynamics, for example, when modeling domain structures [41] or vortex core dynamics [42].

It is possible to use atomistic spin dynamics (ASD) in scenarios where thermal effects play an important role. In ASD, each magnetic lattice site has a magnetic moment, the dynamics of which are simulated with the stochastic LLG equation [43,44]. The magnetic atoms interact with neighboring moments which can be written as an extended Heisenberg Hamiltonian [34,45]. Atomistic modeling has become an essential tool for modeling ultrafast magnetization dynamics [46,47] and temperature-dependent effects such as laser pump-probe experiments [48–50]. However, simulations of systems on μm lengthscales and μs timescales (such as the magnetic grains found in novel magnetic recording media) become computationally expensive, and a finite-temperature micromagnetic approach valid for AFMs is needed.

Notably, dynamic properties can be calculated through finite-temperature approaches, such as the Landau-Lifshitz-Bloch (LLB) equation [51,52], that fundamentally rely on temperature-dependent micromagnetic parameters. Such approaches are especially important in the emerging field of spin caloritronics, concerning the interplay between spin, charge, and heat degrees of freedom. Extensive work already exists using the LLB micromagnetic formalism to model ferro- and ferrimagnets, including for FePt [53,54], GdFeCo [52], and permalloy [55] on device-level length and timescales.

For a multiscale description, the results from an atomistic spin model are used to determine the temperature-dependent interaction parameters in a micromagnetic model based on a continuum free-energy functional. Several methods have been proposed for connecting the atomistic and micromagnetic parameters. For instance, the atomistic and micromagnetic quantities are connected by comparing the spin wave spectrum obtained from the two approaches [56]. Alternatively, the coefficients appearing in the micromagnetic model are temperature-dependent and directly related to experimentally observable quantities such as the macroscopic magnetization,

the domain wall (DW) width, skyrmion radius, or spin spiral wavelength. As an example, the exchange stiffness and the uniaxial anisotropy can be calculated via the temperature dependence of the domain wall width and free energy in an implicit way [57].

Such a multiscale description connecting atomistic spin models to micromagnetism is missing for AFMs. Here, we follow the described multiscale description by comparing macroscopic observable quantities calculated by both the atomistic spin model and the LLB approach. Additionally, the dynamics described by the LLB formalism for AFMs is incomplete. First attempts have been made to calculate the domain wall velocity due to a thermal gradient for a generic AFM using an LLB model [58]. However, the proposed model for AFM-LLB lacks a fundamental aspect of the magnetic properties at finite temperatures, the relaxation of the magnetization length. The correct description of the magnetization quenching dynamics (or longitudinal relaxation dynamics) is essential for the modeling of ultrafast magnetization dynamics and switching. A revised version of the AFM-LLB that includes the recently derived exchange enhanced longitudinal effective damping [59] is necessary in order to extend the LLB framework to AFMs.

Here we present a complete multiscale model of the AFM Mn_2Au . The model starts with parameters from density functional theory (DFT) calculations [60], then going via atomistic spin dynamics to a newly developed LLB equation for AFMs. We calculate the thermal equilibrium properties using ASD and use the results as input into an AFM-LLB model, where instead of having a spin at each atomistic site we simulate a collection of spins, known as a macrospin (in much the same way as is done in traditional LLG-based micromagnetics). This method of starting with first-principles calculations and ending with a description on micromagnetic length scales is known as multiscale modeling. This is the first study of its kind where both the transverse and longitudinal processes of a collinear AFM have been accurately described within an LLB framework.

The work is broken down in the following way. We begin with an introduction of the atomistic spin model with the DFT parameters that are used to parameterize the atomistic Hamiltonian. We then present the transverse terms of the AFM LLB model and present results for the antiferromagnetic resonance (AFMR) and compare to ASD and analytical expressions. We then introduce the longitudinal term in the LLB model and compare the dynamics from ASD and LLB simulations for step changes in temperature as well as for ultrafast laser heating using a two-temperature model. Finally, as an example where both the longitudinal and transverse components of the AFM-LLB are important (and where ASD simulations take orders of magnitude more computational time than an LLB approach) we present a comparison between LLB, ASD and analytical expressions for the DW motion due to a thermal gradient.

II. ATOMISTIC MODEL

The dynamics of each atomistic spin is governed by the stochastic Landau-Lifshitz-Gilbert equation (s-LLG)

equation:

$$\frac{\partial \mathbf{S}_i}{\partial t} = -\frac{\gamma_i}{(1 + \lambda_i^2)\mu_i} [\mathbf{S}_i \times \mathbf{H}_i + \lambda_i \mathbf{S}_i \times (\mathbf{S}_i \times \mathbf{H}_i)], \quad (1)$$

where \mathbf{S}_i is a normalized unit vector of the spin at site i , λ_i is the effective damping parameter, γ_i is the gyromagnetic ratio, μ_i is the atomic magnetic moment and \mathbf{H}_i is the effective field acting on the spin at site i . The effective field is the sum of a fieldlike stochastic term and the negative derivative of the spin Hamiltonian:

$$\mathbf{H}_i = \boldsymbol{\zeta}_i(t) - \frac{\partial \mathcal{H}}{\partial \mathbf{S}_i}, \quad (2)$$

where the Hamiltonian given by:

$$\mathcal{H} = -\sum_{\langle ij \rangle} J_{ij} \mathbf{S}_i \cdot \mathbf{S}_j - d_\eta \sum_i (S_i^\eta)^2 - \mu_s \mathbf{B} \cdot \sum_i \mathbf{S}_i, \quad (3)$$

where J_{ij} is the exchange interaction between site i and site j , \mathbf{B} is the Zeeman field and d_η is the uniaxial anisotropy constant with $\eta = x, y, z$. The stochastic term $\boldsymbol{\zeta}_i(t)$ in Eq. (2) describes the coupling of the spin system to an external thermal bath and accounts for the thermal fluctuations. The noise processes are governed by the equations:

$$\langle \zeta_i^a(t) \zeta_j^b(t') \rangle = 2\delta_{ij} \delta_{ab} \delta(t - t') \frac{\mu_i \lambda_i k_B T}{\gamma_i} \langle \zeta_i^a(t) \rangle = 0, \quad (4)$$

where a and b are the Cartesian components and T is the temperature of the system. The integration of the s-LLG equation is completed using the Heun integration method [61]. \mathbf{S}_i is normalized after both the predictor and corrector step to ensure conservation of the magnetization length. The simulations are performed on an in-house code capable of running on graphical processing units.

For the atomistic simulations of Mn_2Au , we take parameters for the exchange constants, magnetic moment and anisotropy from previous work by Ruta *et al.* [60]. Using the LMTO-ASA method [62], they calculate a strong negative uniaxial anisotropy constant along the z direction, meaning the Néel vector has no preferential direction in the plane. We opt to use an additional uniaxial anisotropy term along the [100] direction induced by in-plane strain with a value of 0.0026 mRyd/Mn as calculated by Shick *et al.* [63]. In such a way, the system has a single favored orientation of the Néel vector. We use the first four nearest-neighbor interactions between Mn sites as illustrated in Fig. 1. The parameters used in the atomistic Hamiltonian can be found in Table I. For the exchange constant J_1, J_2 , and J_3 there are four interactions for each atomic site, and for J_4 there is just one.

III. TRANSVERSE DYNAMICS OF THE ANTIFERROMAGNETIC LANDAU-LIFSHITZ-BLOCH EQUATION

The LLB model captures the dynamics of a collection of exchange coupled atomistic spins, namely the dynamics of thermal averaged $\mathbf{m}_i = \langle \mathbf{S}_i \rangle$. It was first derived by Garanin [51] within a mean-field approximation for ferromagnets, which implies $\mathbf{m}_i = \mathbf{m}$ for lattice sites i . Extensions of the model for nonhomogeneous magnetization states exist within micromagnetic computational approaches [53]. More

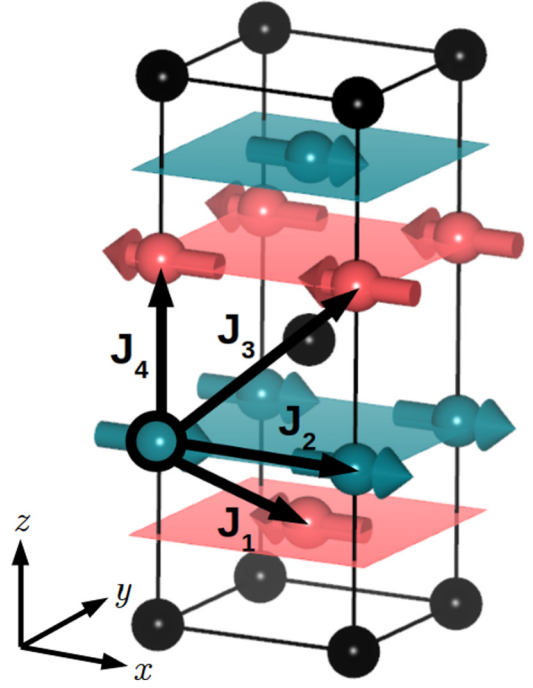


FIG. 1. The Mn_2Au unit cell. The exchange interactions used in this work are labeled J_1 to J_4 . The values can be found in Table I.

recently, the LLB model was extended to ferrimagnets by Atxitia *et al.* [52]. The LLB model contains both transverse and longitudinal relaxation terms and interpolates between Landau-Lifshitz-Gilbert equation at low temperatures (transverse dynamics) and the Bloch equation at high temperatures (longitudinal dynamics). To start with, a comparison of the transverse dynamics between the AFM-LLB and atomistic models is given. We begin with an LLB equation that neglects changes in the magnetization length, and purely describes the transverse dynamics,

$$\frac{d\mathbf{m}_v}{dt} = -\gamma [\mathbf{m}_v \times \mathbf{H}_{\text{eff},v}] - \gamma \alpha_\perp \frac{[\mathbf{m}_v \times [\mathbf{m}_v \times \mathbf{H}_{\text{eff},v}]]}{m_v^2}. \quad (5)$$

The above looks remarkably similar to the LLG equation in that we have a precessional and relaxation term in both models. In the above, \mathbf{m}_v is the macrospin magnetization in

TABLE I. Parameters used in the Hamiltonian for the atomistic modeling of Mn_2Au .

Constant	Value	Unit
Lattice constant, a	3.330	Å
Lattice constant, c	8.537	Å
Magnetic moment, μ_s	3.8663	μ_B
Exchange constant, J_1	-5.3422	mRy
Exchange constant, J_2	0.6484	mRy
Exchange constant, J_3	-0.6341	mRy
Exchange constant, J_4	-6.8986	mRy
Sum of FM exchange, $J_{0,vv}$	2.5934	mRy
Sum of AFM exchange, $J_{0,v\kappa}$	-30.8040	mRy
Uniaxial anisotropy in z direction, d_\parallel	-0.0663	mRy
Uniaxial strain anisotropy in x direction, d_\parallel^*	0.0026	mRy

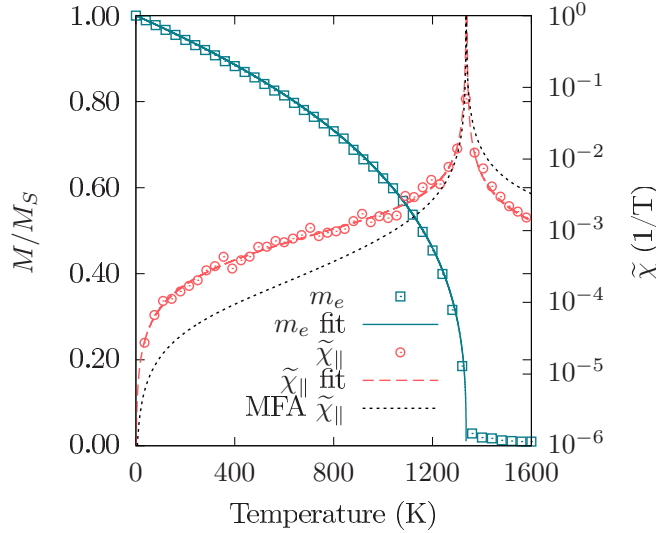


FIG. 2. The sublattice magnetization of Mn_2Au as a function of temperature. The solid line is a fit to the expression $M/M_S = m_e(T) = (1 - T/T_N)^b$. The circular points show the longitudinal susceptibility, $\tilde{\chi}_{||}(T)$, calculated from ASD and the dashed line shows $\tilde{\chi}_{||}(T)$ taken from MFA, which is discussed in Sec. IV.

sublattice v . It is not of constant length and its equilibrium value, $m_e(T)$ is temperature dependent. The dimensionless transverse damping parameter is given by

$$\alpha_{\perp} = \begin{cases} \lambda(1 - \frac{T}{T_N}), & T < T_N \\ \lambda \frac{2T}{T_N}, & T > T_N \end{cases} \quad (6)$$

It is worth noting that for situations where the magnetization length is fairly constant, $m_v = m_{e,v}$, Eq. (5) can be written in terms of a normalized vector, $\mathbf{n}_v = \mathbf{m}_v/m_{e,v}$,

$$\frac{d\mathbf{n}_v}{dt} = -\gamma[\mathbf{n}_v \times \mathbf{H}_{\text{eff},v}] - \gamma \frac{\alpha_{\perp}}{m_{e,v}}[\mathbf{n}_v \times [\mathbf{n}_v \times \mathbf{H}_{\text{eff},v}]], \quad (7)$$

which is identical to the LLG equation [43] with the identification $\alpha_{\text{LLG}} = \alpha_{\perp}/m_e$.

The Néel temperature, T_N , is taken from atomistic simulations of the equilibrium magnetization, $m_e(T)$. For these calculations, we simulate $30 \times 30 \times 30$ unit cells with periodic boundary conditions. The atomistic damping in Eq. (1), λ_i , is set 1.0 for both sublattices to allow for a faster relaxation of the magnetization length. The equilibrium magnetization as a function of temperature can be found in Fig. 2. The fit function, $m_e(T) = (1 - T/T_N)^b$, shown by the solid black line in Fig. 2, has free fitting parameters T_N and b which provide a good estimate of the transition temperature for an infinite system. Fitting to the equilibrium magnetization from ASD yields $T_N = 1335$ K and $b = 0.34$. A more accurate way to determine the critical temperature is through calculations of the parallel susceptibility, $\tilde{\chi}_{||}(T)$. In an atomistic spin model, the parallel susceptibility is found by measuring the fluctuations of the magnetization

$$\tilde{\chi}_{||} = \frac{\mu_s N}{k_B T} (\langle S_{||}^2 \rangle - \langle S_{||} \rangle^2), \quad (8)$$

where $\langle \dots \rangle$ is an ensemble average and $k_B T$ is the thermal energy. Due to the strong uniaxial easy-plane anisotropy in Mn_2Au , the parallel component is taken as the average of the x and y components of the sublattice magnetization. It is worth noting that the thermal equilibrium parameters are the same for both sublattices. A value of $T_N = 1333$ K was extracted from fitting to $\tilde{\chi}_{||}(T)$ calculated from atomistic spin dynamics.

Moving away from atomistic spin dynamics and returning to the discussion of the AFM-LLB model—for a single macrospin containing two sublattices with the magnetization length initialized at $m_v = m_e(T)$, the effective field, $\mathbf{H}_{\text{eff},v}$, in Eq. (5) is given by

$$\mathbf{H}_{\text{eff},v} = \mathbf{B} + \mathbf{H}_{a,v} + \frac{J_{0,v\kappa}}{\mu} \mathbf{\Pi}_{\kappa}, \quad (9)$$

where \mathbf{B} is the applied magnetic field, $\mathbf{H}_{a,v}$ is the anisotropy field, $J_{0,v\kappa}$ is the sum of the interlattice exchange (see Table I), and $\mathbf{\Pi}_{\kappa}$ is given by, $\mathbf{\Pi}_{\kappa} = -[\mathbf{m}_v \times [\mathbf{m}_v \times \mathbf{m}_{\kappa}]]/m_v^2$ where \mathbf{m}_{κ} is the magnetization vector of the second sublattice. The anisotropy field in the macrospin model, $\mathbf{H}_{a,v}$, is defined as $\mathbf{H}_{a,v} = \frac{2K(T)}{M_S}$ where the temperature dependence of the anisotropy constant is governed by Callen-Callen scaling; $K(T) = K(0)m_e^3(T)$ [64].

To validate the temperature-dependent transverse dynamics described by the LLB model, we present simulation results showing the temperature dependence of the AFMR for Mn_2Au using both atomistic s-LLG and AFM-LLB models, as well as a comparison to the Kittel equation for AFMR [11,12]. Magnetic oscillations in AFMs have a resonance frequency in the THz range, orders of magnitude faster than the GHz range observed in ferromagnets. As a result of the complexity in current THz-signal generation methods [65–67], AFM oscillators have been proposed for use in adjustable room-temperature THz-frequency signal devices [13–15]. While attempts to experimentally measure the in-plane AFMR in Mn_2Au driven by Néel spin orbit torques have previously failed [68], it piqued the magnetism community's interest, highlighting the importance of not only measuring, but also calculating, the resonant frequency in AFMs. Since the AFMR sets the speed limit of the AFM dynamics, it is highly relevant for the development of ultrafast memory applications. For the atomistic simulations of the AFMR, the system is initially set to relax to its equilibrium magnetization for each given temperature. Once relaxed, all spins are rotated by 20° out of the easy plane inducing a torque and thereby exciting the AFMR mode. The relaxation time of the transverse motion, τ_{\perp} , can be related to the effective field and transverse damping via

$$\tau_{\perp} = \frac{m_e}{\alpha_{\perp} \omega_{\text{ex}}}, \quad (10)$$

where $\omega_{\text{ex}} = \gamma H_E = \gamma \frac{J_{0,v\kappa}}{\mu_s} m_e$. An example of the m_z dynamics at $T = 0$ K can be seen in Fig. 3. The value of τ_{\perp} was found by fitting the sublattice magnetization to the equation $m_z(t)/m_e = \cos(\omega_{\text{AFMR}} t) \exp(-t/\tau_{\perp})$.

A comparison of the temperature dependence of τ_{\perp} can be found in Fig. 4. We calculate τ_{\perp} atomistically for values of $\lambda = 0.05, 0.01$, and 0.001 . Note for lower values of λ we see a reduction in the relaxation time as we approach T_N . This effect is explained by the fact at lower damping

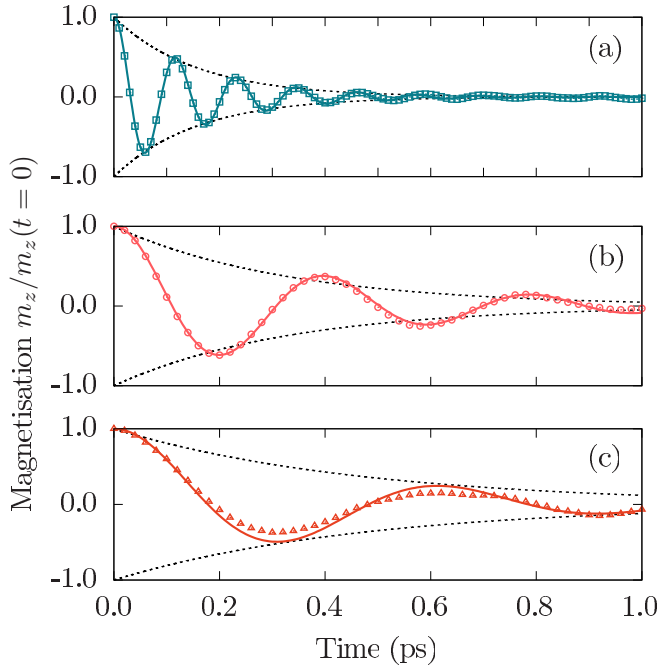


FIG. 3. The m_z motion following a rotation of both sublattices by 20° out of the easy plane at (a) $T = 300$ K, (b) $T = 1000$ K, and (c) $T = 1200$ K. Solid line are the AFM-LLB model and points are ASD. The dotted line shows the relaxation of the transverse dynamics. The relaxation time can be related to α_\perp through with Eq. (10).

we are further from equilibrium with the thermal bath and energy is predominantly transferred between the sublattices. This effect is enhanced as the temperature increases, and so the transverse spin fluctuations of each sublattice out of the antiparallel alignment at the atomic level. For low damping, these atomic spin fluctuations survive longer, which allows for further transfer of angular momentum between sublattices beyond that described by Eq. (10). This angular momentum

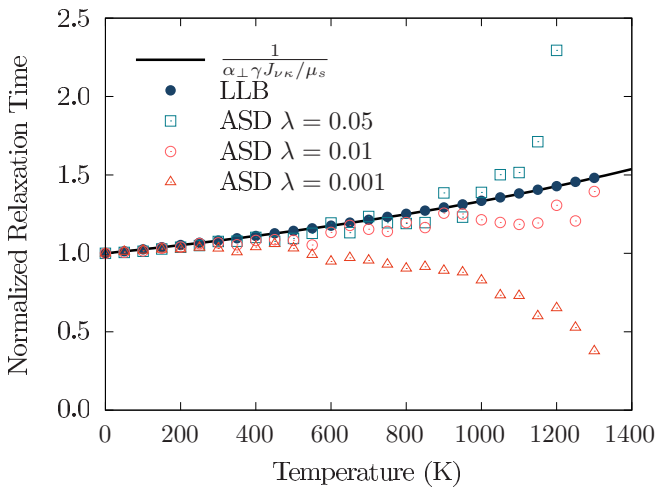


FIG. 4. The transverse relaxation time, τ_\perp as function of temperature. Empty points represent ASD simulations with values of $\lambda = 0.05$ (square), 0.01 (circle), and 0.001 (triangles). Solid circles are the AFM-LLB model. The solid line is given by Eq. (10).

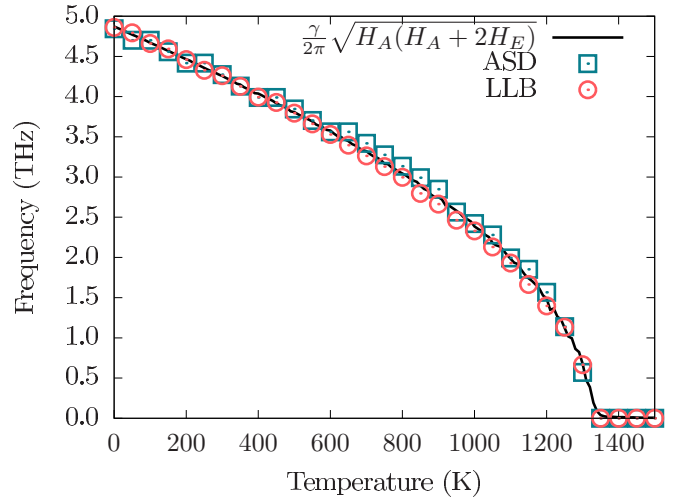


FIG. 5. AFMR frequency of Mn_2Au . The solid line is the result from Eq. (11), square points are from ASD, and circular points are the LLB simulations respectively.

transfer is not along the longitudinal component, but rather the transverse direction. Although the ASD model naturally captures this effect, in our macroscopic model we do not take into account this effect. However, the effect of these transverse spin fluctuations will play a decisive role in the longitudinal dynamics, which will be discussed at length in Sec. IV. The temperature dependence of τ_\perp in the LLB model is independent of λ . The exact form of the damping dependence on τ_\perp remains an open question.

The AFMR frequency of the dynamics was extracted via fast Fourier transform of m_z of a single sublattice. The results of this frequency analysis can be found in Fig. 5 showing excellent agreement between the models and the analytical expression. The analytic expression for the AFMR, shown by the solid line in Fig. 5, is given by:

$$f = \frac{\gamma}{2\pi} \sqrt{H_A(H_A + 2H_E)}, \quad (11)$$

where H_A and H_E are the anisotropy and exchange fields, respectively.

IV. LONGITUDINAL RELAXATION

It has been demonstrated that a femtosecond laser-pulse can induce ultrafast magnetization dynamics in ferro- and ferrimagnets [17,46,47]. While mechanisms leading to the ultrafast demagnetization in magnetic materials broadly are still under debate, in certain ferrimagnets, a single laser-pulse can induced switching of the magnetization [46]. The magnetic order dynamics in AFMs, i.e., Néel vector length dynamics, is less known. In order to describe the magnetic order quenching in Mn_2Au , we introduce a term in the LLB equation that accounts for changes in the magnetization length. Here we are only interested in the longitudinal dynamics—parallel to the magnetization direction—and can therefore ignore the transverse terms,

$$\frac{d\mathbf{m}_v}{dt} = \gamma \alpha_{\parallel}^{\text{AF}} \frac{(\mathbf{m}_v \cdot \mathbf{H}_{\text{eff},v})}{m_v^2} \mathbf{m}_v. \quad (12)$$

The effective field for a purely longitudinal relaxation (where one can ignore any external, anisotropy or intermacrospin exchange fields) is given by

$$\mathbf{H}_{\text{eff},v}^{\parallel} = \begin{cases} \frac{1}{2\tilde{\chi}_{\parallel}} \left(1 - \frac{m_v^2}{m_c^2}\right) \mathbf{m}_v, & T \lesssim T_N \\ -\frac{1}{\tilde{\chi}_{\parallel}} \left(1 + \frac{3}{5} \frac{T_N}{T-T_N} m_v^2\right) \mathbf{m}_v, & T \gtrsim T_c \end{cases}, \quad (13)$$

where $\tilde{\chi}_{\parallel}$ is the reduced longitudinal susceptibility. In this work we opt to use the susceptibility taken from a MFA [69]. We find that the agreement in the longitudinal relaxation between ASD and LLB when using $\tilde{\chi}_{\parallel}$ taken from ASD simulations gave large discrepancies between the two models at lower temperature while using $\tilde{\chi}_{\parallel}$ taken from a MFA gave excellent agreement for all temperatures. This problem has been noted elsewhere: Vogler *et al.* mention that calculations of $\tilde{\chi}_{\parallel}$ only work for hard magnetic materials with strong uniaxial anisotropy [70] with similar problems having been identified in ferrimagnets [71]. The reason for the difference is unclear, and should be investigated as part of future work. The method of calculating the MFA longitudinal susceptibility follows directly from Reference [72]. Using the same value for the exchange constants in ASD and MFA approaches yields a higher critical temperature compared to the atomistic results ($T_N^{\text{MFA}} > T_N^{\text{ASD}}$). Therefore, we rescale the exchange constant to match the value for the Néel temperature extracted from Fig. 2. The process of using a scaled MFA susceptibility has been seen previously in atomistic modeling of GdFeCo [73]. Returning to the discussion of the longitudinal relaxation in the LLB equation, assuming that the macrospin magnetization remains along single axis, $\mathbf{m}_v = [m_v, 0, 0]$, Eq. (12) simplifies to

$$\frac{dm_v}{dt} = \gamma \alpha_{\parallel}^{\text{AF}} H_{\text{eff},v}^{\parallel}. \quad (14)$$

Experimental works studying the ultrafast magnetic order dynamics in the FM and AFM phases of Dy have shown that the AFM phase exhibits faster dynamics than the FM phase [18]. This speed up is attributed to the exchange of angular momentum between sublattices. For Mn₂Au, it will be difficult to conduct a similar comparative study due to the absence of a FM phase. However, a recent theoretical work by Jakobs and Atxitia [59] has concluded that the speed up of the AFM dynamics comes from the exchange-enhancement of the effective damping parameter

$$\alpha_{\parallel}^{\text{AF}} = \alpha_{\parallel}^{\text{FM}} \left(1 + \frac{2}{z|m_v|^{\beta}}\right), \quad (15)$$

where $\alpha_{\parallel}^{\text{FM}}$ is the ferromagnetic longitudinal damping parameter (where the relaxation is solely due to the dissipation of angular momentum to the heat bath) and is defined by

$$\alpha_{\parallel}^{\text{FM}} = \lambda \frac{2T}{3T_N}. \quad (16)$$

In Eq. (15), theory predicts that z is the number of nearest neighbors antiferromagnetically coupled to a given spin. While for a simple cubic with only nearest neighbors this number is 6, for Mn₂Au this would correspond to 5, as sketched in Fig. 1. Our simulations show that $z \approx 6.0$. The exponent β in Eq. (15) is a phenomenological parameter, nec-

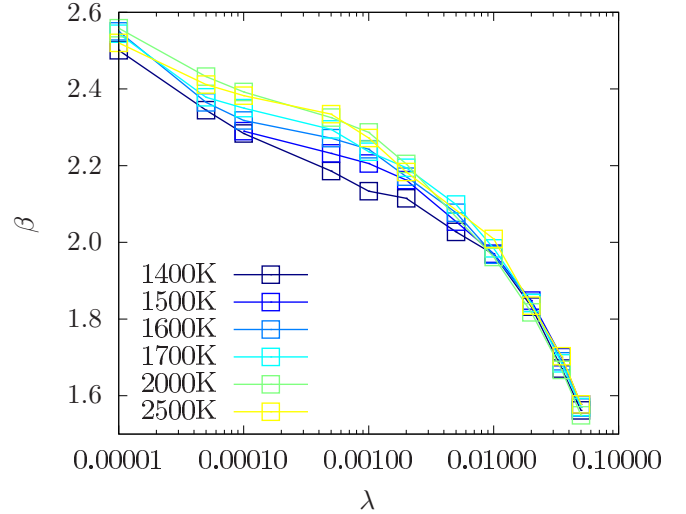


FIG. 6. The damping dependence of β . The MFA LLB equation [51] is fitted to the longitudinal dynamics from atomistic simulations following a step change in temperature from $T = 0$ K to $T > T_N$. All other parameters in the LLB besides β remain fixed.

essary for the description of high nonequilibrium situations where the temperature goes well above the critical temperature. While for small deviations from the equilibrium of the magnetic order parameter, $\beta = 1$, for larger deviations, for example when the temperature of the system changes from $T = 0$ K to $T = 2T_N$, the exponent takes a value of around 2. We also find that alongside the temperature dependence of the β exponent, it also exhibits a damping dependence, which can be found in Fig. 6. To determine the damping dependence of β , numeric solutions of the LLB equation after step change in temperature from $T = 0$ K to $T > T_N$ were fitted against the corresponding atomistic simulations. For the fitting, we use a MFA form of the effective field that is not dependent on any atomistically derived parameters. Instead of using Eq. (13), the effective field is given by [52]

$$H_{\text{eff},v}^{\parallel} = \frac{(m_v - m_{0,v})}{\mu_s \beta L'(\xi_v)} \quad (17)$$

in the above, $m_{0,v}$ is not the equilibrium magnetization and is given by $m_{0,v} = L(\xi_v)$, where $L(\xi_v) = \coth(\xi_v) - 1/\xi_v$ is the Langevin function and $L'(\xi_v) = dL/d\xi_v$ with $\xi_v = \beta \mu_s H_v^{\text{MFA}}$ and $\beta = 1/k_B T$. The MFA field is defined as $H_v^{\text{MFA}} = 3k_B T_N m_c$ [51].

Using the results of our determination of β for a value of $\lambda = 0.01$ we have furthermore carried out simulations of the longitudinal dynamics after a temperature step (Fig. 7). In these temperature step simulations, we begin with a perfectly ordered AFM configuration of Mn₂Au at $T = 0$ K, we then apply a temperature step and record the relaxation to the equilibrium magnetization. Figure 7 shows the longitudinal relaxation for five different temperatures (with $\lambda = 0.01$ for all simulations), the points are simulations using the stochastic LLG equation and the solid lines are from the LLB model. The agreement at lower temperatures is excellent. At temperatures well above T_N , finite-size effects lead to a longer relaxation time in the atomistic model. It is also worth stressing that

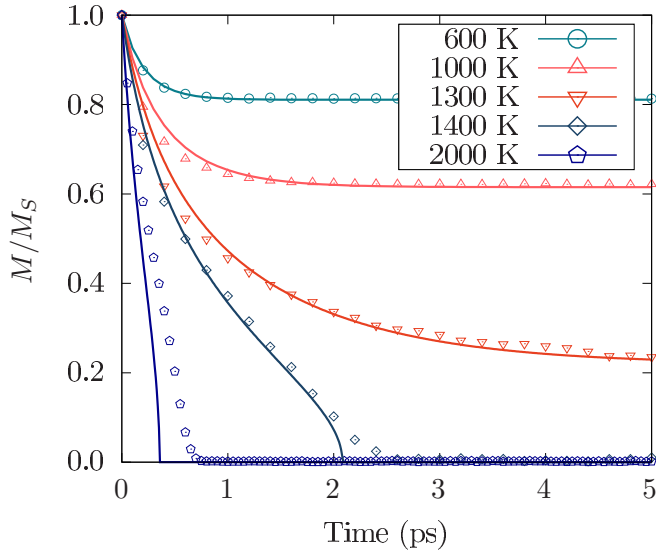


FIG. 7. A comparison at five different temperatures between the AFM-LLB and the atomistic modeling. Symbols represent the atomistic spin dynamics results and the solid lines correspond to the AFM-LLB. No stochastic noise was present in the AFM-LLB simulations.

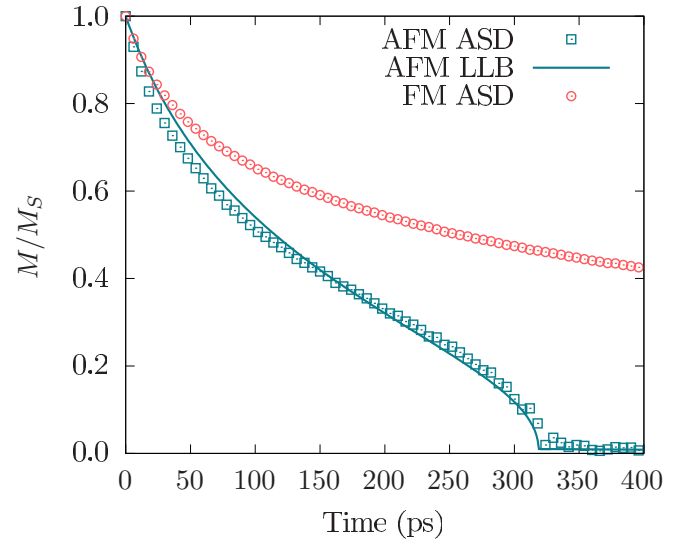


FIG. 8. The longitudinal relaxation following a step change in temperature from 0 K to 1400 K. The Gilbert damping was set to 0.00005. Square points are from ASD simulations of the ground state AFM configuration of Mn_2Au . Circular points are from ASD simulations representing an FM configuration of Mn_2Au where the absolute values of J_1 to J_4 have been used. The solid line shows the AFM-LLB.

instantaneous step changes in temperature from 0 Kelvin to near T_N are radical, and some disagreement would be expected. The reasonable damping value of $\lambda = 0.01$ has been chosen in accordance with previous atomistic modeling of Mn_2Au [74,75].

To highlight the importance of the β exponent in Eq. (15), we performed ASD and LLB simulations with values for $\lambda = 0.00005$ for a step change to above the critical temperature, as shown in Fig. 8. We also include ASD results for an entirely ferromagnetic exchange to show the difference in the relaxation rates between FM and AFM. We find that relaxation dynamics in AFMs is defined by two distinct processes, (i) a exponential decay due to dissipation of angular momentum to the heat-bath and (ii) a power-law decay due to angular momentum exchange between sublattices. While for the FM version of Mn_2Au the relaxation dynamics is described by an exponential decay, for AFMs, the exponential decay only dominates for values of the order parameter $n > 1/3$. As the magnetic order reduces to small values, the rate of angular momentum dissipation remains constant, $(\mu_{\text{at}}/\gamma)\dot{n} \approx (2/3)\lambda k_B T/n^{\beta-1}$, leading to a power-law decay.

Although in the simulations a steplike increase of temperature is easy to achieve, experimentally, a strong and rapid heating of the system is possible by applying, for example, a femtosecond laser pulse. In these scenarios the temperature of the system is difficult to determine, however, given semiclassical considerations [76] one can define a temperature of an electron and a phonon bath. A laser pulse will couple more strongly to the electron system giving large and rapid temperature increases, in hundreds of femtoseconds, to a temperature above T_N ; however, the electron system also quickly cools down on the picosecond time scale by transferring energy to the phonon system via electron-phonon coupling. The electronic temperature is calculated using a two-temperature

model (TTM) [77]. Fig. 9 shows the longitudinal magnetization dynamics for a transient change in temperature following heating from a laser pulse. We begin at $T = 300$ K then heat to just below and above T_N , shown as TTM 1 and TTM 2 in Fig. 9. What is also worth noting is that the AFM-LLB

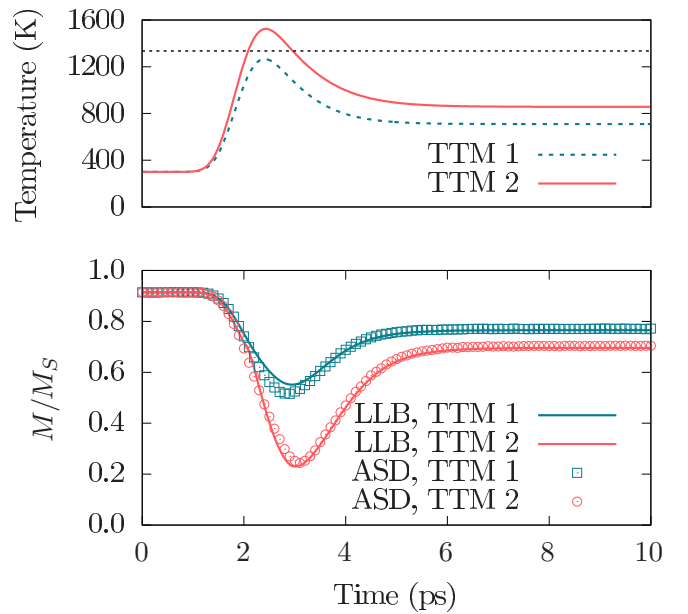


FIG. 9. Top: The electronic temperature dynamics using a TTM. Dotted line shows the Néel temperature. Bottom: Magnetization dynamics from atomistic simulations (black squares) and the LLB equation using a ferromagnetic (dotted lines) and ferrimagnetic (solid lines).

accurately captures both remagnetization and demagnetization processes.

These results show that the exchange-enhanced damping derived by Jakobs and Atxitia is successful in describing the faster relaxation times within the LLB model, especially at lower temperatures. It also shows good agreement when using a TTM, which is highly applicable to simulations of all-optical switching in AFMs.

V. DOMAIN WALL MOTION

The manipulation of DW have been proposed for use in the next generation of logic and memory devices [78,79]. The motion of the DWs can be modulated using spinwaves [80,81], spin currents [82–84] or external magnetic fields [85,86], for example. Another possibility is to drive DW motion by thermal gradients [87,88]. Under thermal gradient, motion of the domain wall is induced toward the hotter end of the nanowire due to a reduction in the free energy, $\Delta F(T)$. For large thermal gradients in ferromagnets, there is a precession of the internal magnetization, which leads to a reduction in the domain wall velocity, known as the Walker breakdown [85]. In previous ASD simulations of AFMs, it has been shown that there is no breakdown in the DW velocity due to symmetry of the torques acting on the DW [89], meaning DWs in AFMs are able to reach higher speeds.

Conventional micromagnetic methods have limitations in the modeling of thermally driven DWs, as they cannot account for the dynamic changes in the magnetization length. It has been shown experimentally that ultrashort laser pulses are able to drive DW motion [88]. In these scenarios, heating and cooling will play a role, and the effects of this cannot be captured using an LLG-based micromagnetic model. This could be simulated using an atomistic approach, but the calculations are expensive and require large ensembles to reduce statistical noise. The LLB model overcomes these issues, making it an important tool for temperature dependant calculations of topological structures such as domain wall, spin-spirals, and skyrmions. As an example of simulations that require both accurate descriptions of the longitudinal and transverse dynamics, we present a comparison of the DW motion under a thermal gradient using both atomistic and AFM-LLB models and compare to previously derived analytical expressions for the DW velocity. As we are considering both longitudinal and transverse dynamics, the LLB equation now reads

$$\begin{aligned} \frac{d\mathbf{m}_v}{dt} = & \gamma[\mathbf{m}_v \times \mathbf{H}_{\text{eff},v}] - \gamma\alpha_{\parallel}^v \frac{(\mathbf{m}_v \cdot \mathbf{H}_{\text{eff},v})}{m_v^2} \mathbf{m}_v \\ & - \gamma\alpha_{\perp}^v \frac{[\mathbf{m}_v \times [\mathbf{m}_v \times \mathbf{H}_{\text{eff},v}]]}{m_v^2} \end{aligned} \quad (18)$$

To be able to describe DWs within an LLB framework, we introduce a term into the LLB Hamiltonian that describes the exchange coupling between neighboring macrospins that is given by:

$$\mathbf{H}_{\text{ex}}^{v,i} = \frac{2A(T)}{d^2 M_S m_e^2} \sum_j (\mathbf{m}_{v,j} - \mathbf{m}_{v,i}), \quad (19)$$

where $A(T)$ is the exchange stiffness, d^2 is the surface area between neighboring macrospins, and M_S is the saturation

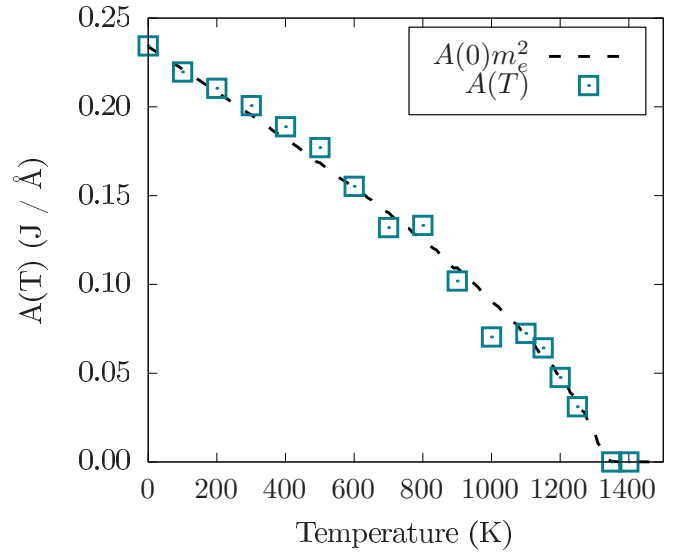


FIG. 10. Exchange stiffness as a function of temperature from atomistic simulations. Dotted line shows the proportionality to the equilibrium magnetization with $A(0)$ taken from Eq. (22).

magnetization. The value and temperature dependence of the exchange stiffness is calculated using atomistic simulations of the DW width, δ_0 . The relation that links the DW width to the exchange stiffness is given by

$$\delta_0(T) = \sqrt{\frac{A(T)}{K(T)}}, \quad (20)$$

where $K(T)$ is the anisotropy energy where again we use Callen-Callen scaling [64], $K(T) = Km_e^3(T)$. The exchange stiffness, $A(T)$ scales with m_e^2 within a MFA. Figure 10 shows the exchange stiffness as a function of temperature with points representing atomistic simulation results, and the dotted line showing the scaling law m_e^2 .

For the atomistic simulations of the domain wall width, we ensure the length of the system in the x direction is much wider than the zero Kelvin domain wall width. The Mn sites at the left boundary of the slab remain fixed in an antiparallel alignment to the spins at the right boundary. The remainder of the spins are allowed to relax to form a domain wall profile. The reduced magnetization, $m(x)$, is then fitted to a hyperbolic tangent function to find the width parameter:

$$m(x) = m_e \tanh\left(\frac{x-b}{\delta_0}\right), \quad (21)$$

where b is the central position of the DW and δ_0 is the wall-width parameter. A comparison of the DW profile at $T = 0$ K can be found in Fig. 11. The Néel wall width can be related to the wall width parameter through $\delta = \pi\delta_0$. We calculate $\delta(0) = 31.2$ nm from atomistic simulations and see good agreement between ASD and LLB in Fig. 11 for intermediate and high temperatures.

It is possible to relate the zero temperature exchange stiffness $A(0)$ directly to the J_{ij} values and lattice constants found

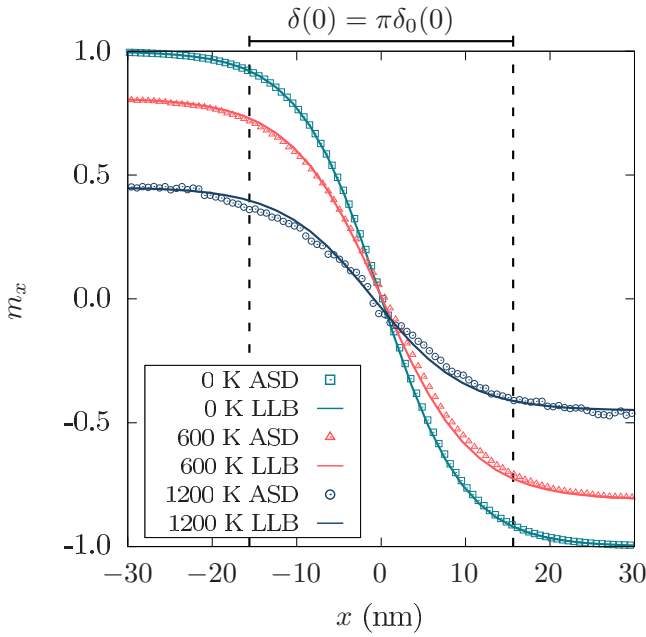


FIG. 11. The domain wall width at 0 K, 600 K, and 1200 K. Solid lines are from LLB simulations and points are from ASD. The Néel domain wall width is given by $\delta(T) = \pi \delta_0(T)$. The dotted lines show the width of the domain wall at 0 K.

in Table I through the equation [57]

$$A(0) = \frac{1}{V_0} \sum_{i,v} \frac{|J_{i,v}|}{(a_{i,v})^2}, \quad (22)$$

where V_0 is the unit cell volume, v represents all the neighbors for site i where x or y are nonzero as the domain wall forms in the xy plane, and a_v is the absolute distance between site i and site v . In total, there are 12 interactions that contribute to $A(0)$. Referring to Fig. 1, the only interaction that does not contribute is J_4 . Using the values for J_1 to J_3 in Table I yields $A(T = 0 \text{ K}) = 2.34 \times 10^{-11} \text{ J/m}$, which agrees well with calculations of the exchange stiffness through atomistic simulations of the DW width, as shown in Fig. 10. We should emphasize here that we use a different equation for the exchange coupling to Chen *et al.* [58]. They use an exchange term that sums over the opposite sublattice in the neighboring macrospins. This term would be nonzero when sublattices in neighboring macrospins are parallel, leading to a disagreement between LLB and ASD simulations of the AFMR (see Sec. II).

For the atomistic calculations of the DW velocity, we begin with a DW initialized at 0 Kelvin along the x direction, we then apply a linear thermal gradient in the direction of the DW. It has been shown that the DW velocity induced by a thermal gradient in an AFM can be approximated by [90]

$$v_{\text{DW}}^{\text{LLB}} = \frac{2\gamma}{M_s \alpha_{\perp}} \frac{\partial T}{\partial z} \frac{\partial A}{\partial T}. \quad (23)$$

As seen in previous analyses of domain walls [89,90], the weak temperature dependence of α_{\perp} is neglected and the exchange stiffness is linearized to $dA/dT \approx A(0)/T_C$. Figure 12 shows the domain wall velocity for Mn_2Au in atomistic and LLB simulations due to a thermal gradient, showing good

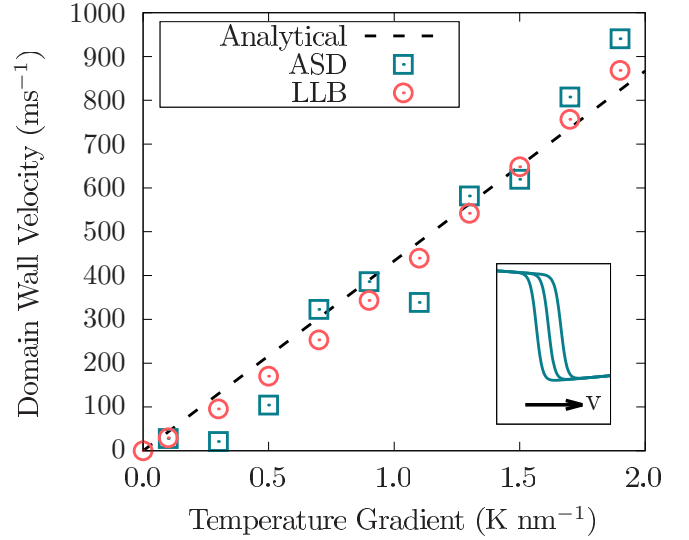


FIG. 12. Domain wall velocity as a function of the temperature gradient. λ was set to 0.01 for the simulations. The solid line is given by Eq. (23). The inset shows an example of the domain wall at three different timesteps. The wall is moving from left to right in the figure.

agreement with Eq. (23). The velocity is calculated by, once again, fitting the DW profile to Eq. (21) to find the center of the domain wall, then tracking the movement of this central position in time. While the relation appears linear in Fig. 12, in reality the velocity will reach a saturation point governed by the magnon group velocity [91]. In the atomistic modeling of thermally induced DW motion, Selzer *et al.* [89] state that there is no acceleration phase, and the DW moves with constant velocity, which is what we observe in Mn_2Au in both LLG and LLB simulations.

VI. SUMMARY

Using a multiscale approach, it has been demonstrated that antiferromagnets such as Mn_2Au can be modelled micromagnetically on micrometer length scales using an AFM-LLB model. We started with parameters from previous work for the exchange, anisotropy, and magnetic moment which were fed into an atomistic model of Mn_2Au . Then we calculated the temperature-dependent parameters $m_e(T)$, $A(T)$, $\tilde{\chi}_{\parallel}(T)$ using atomistic spin dynamics before using these as input into the AFM-LLB.

To verify the dynamics described by the proposed LLB model for Mn_2Au , first we presented consistent results among ASD, LLB, and the Kittel relation for the antiferromagnetic resonance frequency. As well as serving as a validation of the transverse dynamics, we have revealed the first estimate of the in-plane AFMR frequency in Mn_2Au . The fact the resonant frequency sits within the THz range opens the possibility subpicosecond switching and generation of THz electromagnetic signals at ambient temperatures. Second, we compared ASD simulations results to the AFM-LLB model for the longitudinal dynamics following step changes in temperature and laser pulse heating, both of which give excellent agreement between the models. Finally, we provided a comparison of the domain wall motion due to a thermal gradient as an example

of how the LLB model for an AFM can be utilised on μm length and μs timescales, opening the door to micromagnetic simulations of AFM materials for use in realistic spintronic devices. While questions such as the damping dependence of the transverse relaxation time, and the poor agreement for the longitudinal relaxation between ASD and LLB with $\tilde{\chi}$ from ASD remain unanswered, the AFM-LLB opens the possibility for the description laser induced local thermal gradients on length-scales and the benchmark of other thermodynamic effects in collinear AFMs on micrometer length-scales.

Mn_2Au has been chosen as an exemplar material for this study due to its interest from the magnetism community, its simple collinear structure and uncomplicated anisotropy. For other simple collinear AFM, such as CuMnAs , the calculation of the temperature-dependent functions $m_e(T)$, $A(T)$, $\tilde{\chi}_{\parallel}(T)$ is straightforward and the present theory would be sufficient for modeling the magnetization dynamics using the AFM-LLB. The temperature dependence of the anisotropy is also required for the AFM-LLB model. For Mn_2Au , the anisotropy is uniaxial easy-plane with an additional strain anisotropy making it uniaxial easy-axis and scales according to the Callen-Callen law. For more complex anisotropies, the temperature dependence can be calculated using atomistic Monte Carlo methods

[92,93]. For more complex AFM systems, where there may be more than two sublattices or the moments exist in a non-collinear configuration, a careful study of the AFM properties is necessary, as well as an extension of the current theory.

ACKNOWLEDGMENTS

This work was supported by the EPSRC TERASWITCH project (Project ID EP/T027916/1). Simulations were undertaken using the HPC cluster at Sheffield Hallam University and resources provided by the Cambridge Tier-2 system operated by the University of Cambridge Research Computing Service funded by EPSRC Tier-2 capital Grant No. EP/P020259/1. U.A. gratefully acknowledges support by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) Project-ID 328545488TRR 227, Project No. A08. J.H. and U.A. acknowledge support from European COST Action CA17123 “Magneto-fon” and the short-time scientific mission awarded to J.H. U.A. gratefully acknowledges support by grant PID2021-122980OB-C55 and the grant RYC-2020-030605-I funded by MCIN/AEI/10.13039/501100011033 and by “ERDF A way of making Europe” and “ESF Investing in your future.”

- [1] I. Dzyaloshinskii, Theory of helicoidal structures in antiferromagnets. i. Nonmetals, *Sov. Phys. JETP* **19**, 960 (1964).
- [2] S. Chakravarty, B. I. Halperin, and D. R. Nelson, Low-Temperature Behavior of Two-Dimensional Quantum Antiferromagnets, *Phys. Rev. Lett.* **60**, 1057 (1988).
- [3] E. Manousakis, The spin-1/2 heisenberg antiferromagnet on a square lattice and its application to the cuprous oxides, *Rev. Mod. Phys.* **63**, 1 (1991).
- [4] F. Krizek, S. Reimers, Z. Kašpar, A. Marmodoro, J. Michalička, O. Man, A. Edström, O. J. Amin, K. W. Edmonds, R. P. Campion, F. Maccheronzi, S. S. Dhesi, J. Zubáč, D. Kriegner, D. Carbone, J. Železný, K. Výborný, K. Olejník, V. Novák, J. Ruzs *et al.*, Atomically sharp domain walls in an antiferromagnet, *Sci. Adv.* **8**, eabn3535 (2022).
- [5] J. Železný, H. Gao, K. Výborný, J. Zemen, J. Mašek, A. Manchon, J. Wunderlich, J. Sinova, and T. Jungwirth, Relativistic Néel-Order Fields Induced by Electrical Current in Antiferromagnets, *Phys. Rev. Lett.* **113**, 157201 (2014).
- [6] X. Marti, I. Fina, C. Frontera, J. Liu, P. Wadley, Q. He, R. J. Paull, J. D. Clarkson, J. Kudrnovský, I. Turek, J. Kuneš, D. Yi, J.-H. Chu, C. T. Nelson, L. You, E. Arenholz, S. Salahuddin, J. Fontcuberta, T. Jungwirth, and R. Ramesh, Room-temperature antiferromagnetic memory resistor, *Nat. Mater.* **13**, 367 (2014).
- [7] W. Legrand, D. Maccariello, F. Ajejas, S. Collin, A. Vecchiola, K. Bouzehouane, N. Reyren, V. Cros, and A. Fert, Room-temperature stabilization of antiferromagnetic skyrmions in synthetic antiferromagnets, *Nat. Mater.* **19**, 34 (2020).
- [8] P. Němec, M. Fiebig, T. Kampfrath, and A. V. Kimel, Antiferromagnetic opto-spintronics, *Nat. Phys.* **14**, 229 (2018).
- [9] J. Železný, P. Wadley, K. Olejník, A. Hoffmann, and H. Ohno, Spin transport and spin torque in antiferromagnetic devices, *Nat. Phys.* **14**, 220 (2018).
- [10] J. Li, R. J. Green, Z. Zhang, R. Sutarto, J. T. Sadowski, Z. Zhu, G. Zhang, D. Zhou, Y. Sun, F. He, S. Ramanathan, and R. Comin, Sudden Collapse of Magnetic Order in Oxygen-Deficient Nickelate Films, *Phys. Rev. Lett.* **126**, 187602 (2021).
- [11] C. Kittel, On the theory of ferromagnetic resonance absorption, *Phys. Rev.* **73**, 155 (1948).
- [12] F. Keffer and C. Kittel, Theory of antiferromagnetic resonance, *Phys. Rev.* **85**, 329 (1952).
- [13] J. Chęciński, M. Frankowski, and T. Stobiecki, Antiferromagnetic nano-oscillator in external magnetic fields, *Phys. Rev. B* **96**, 174438 (2017).
- [14] R. Cheng, D. Xiao, and A. Brataas, Terahertz Antiferromagnetic Spin Hall Nano-Oscillator, *Phys. Rev. Lett.* **116**, 207603 (2016).
- [15] R. Khymyn, I. Lisenkov, V. Tiberkevich, B. A. Ivanov, and A. Slavin, Antiferromagnetic THz-frequency josephson-like oscillator driven by spin current, *Sci. Rep.* **7**, 43705 (2017).
- [16] T. Kampfrath, A. Sell, G. Klatt, A. Pashkin, S. Mährlein, T. Dekorsy, M. Wolf, M. Fiebig, A. Leitenstorfer, and R. Huber, Coherent terahertz control of antiferromagnetic spin waves, *Nat. Photon.* **5**, 31 (2011).
- [17] E. Beaurepaire, J.-C. Merle, A. Daunois, and J.-Y. Bigot, Ultrafast Spin Dynamics in Ferromagnetic Nickel, *Phys. Rev. Lett.* **76**, 4250 (1996).
- [18] N. Thielemann-Kühn, D. Schick, N. Pontius, C. Trabant, R. Mitzner, K. Holldack, H. Zabel, A. Föhlisch, and C. Schüßler-Langeheine, Ultrafast and Energy-Efficient Quenching of Spin Order: Antiferromagnetism Beats Ferromagnetism, *Phys. Rev. Lett.* **119**, 197202 (2017).
- [19] M. Meinert, D. Graulich, and T. Matalla-Wagner, Electrical Switching of Antiferromagnetic Mn_2Au and the Role of Thermal Activation, *Phys. Rev. Appl.* **9**, 064040 (2018).
- [20] X. Chen, S. Shi, G. Shi, X. Fan, C. Song, X. Zhou, H. Bai, L. Liao, Y. Zhou, H. Zhang, A. Li, Y. Chen, X. Han, S. Jiang, Z. Zhu, H. Wu, X. Wang, D. Xue, H. Yang, and F. Pan, Observation of the antiferromagnetic spin hall effect, *Nat. Mater.* **20**, 800 (2021).

- [21] V. Grigorev, M. Filianina, S. Y. Bodnar, S. Sobolev, N. Bhattacharjee, S. Bommanaboyena, Y. Lytvynenko, Y. Skourski, D. Fuchs, M. Kläui, M. Jourdan, and J. Demsar, Optical Readout of the Néel Vector in the Metallic Antiferromagnet Mn_2Au , *Phys. Rev. Appl.* **16**, 014037 (2021).
- [22] F. Máca, J. Mašek, O. Stelmakhovich, X. Martí, H. Reichlová, K. Uhlířová, P. Beran, P. Wadley, V. Novák, and T. Jungwirth, Room-temperature antiferromagnetism in CuMnAs , *J. Magn. Magn. Mater.* **324**, 1606 (2012).
- [23] K. Olejník, V. Schuler, X. Martí, V. Novák, Z. Kašpar, P. Wadley, R. P. Campion, K. W. Edmonds, B. L. Gallagher, J. Garces, M. Baumgartner, P. Gambardella, and T. Jungwirth, Antiferromagnetic CuMnAs multi-level memory cell with micro-electronic compatibility, *Nat. Commun.* **8**, 15434 (2017).
- [24] M. J. Grzybowski, P. Wadley, K. W. Edmonds, R. Beardsley, V. Hills, R. P. Campion, B. L. Gallagher, J. S. Chauhan, V. Novak, T. Jungwirth, F. Maccherozzi, and S. S. Dhesi, Imaging Current-Induced Switching of Antiferromagnetic Domains in CuMnAs , *Phys. Rev. Lett.* **118**, 057701 (2017).
- [25] S. Yu. Bodnar, L. Šmejkal, I. Turek, T. Jungwirth, O. Gomonay, J. Sinova, A. A. Sapozhnik, H.-J. Elmers, M. Kläui, and M. Jourdan, Writing and reading antiferromagnetic Mn_2Au by Néel spin-orbit torques and large anisotropic magnetoresistance, *Nat. Commun.* **9**, 348 (2018).
- [26] S. P. Bommanaboyena, D. Backes, L. S. I. Veiga, S. S. Dhesi, Y. R. Niu, B. Sarpi, T. Denneulin, A. Kovács, T. Mashoff, O. Gomonay, J. Sinova, K. Everschor-Sitte, D. Schöнке, R. M. Reeve, M. Kläui, H.-J. Elmers, and M. Jourdan, Readout of an antiferromagnetic spintronics system by strong exchange coupling of Mn_2Au and Permalloy, *Nat. Commun.* **12**, 6539 (2021).
- [27] V. M. Barthem, C. V. Colin, H. Mayaffre, M. H. Julien, and D. Givord, Revealing the properties of Mn_2Au for antiferromagnetic spintronics, *Nat. Commun.* **4**, 2892 (2013).
- [28] P. Wadley, V. Hills, M. R. Shahedkhah, K. W. Edmonds, R. P. Campion, V. Novák, B. Ouladdiaf, D. Khalyavin, S. Langridge, V. Saidl, P. Nemec, A. W. Rushforth, B. L. Gallagher, S. S. Dhesi, F. Maccherozzi, J. Železný, and T. Jungwirth, Antiferromagnetic structure in tetragonal CuMnAs thin films, *Sci. Rep.* **5**, 17079 (2015).
- [29] G. Kresse and J. Hafner, *Ab initio* molecular dynamics for liquid metals, *Phys. Rev. B* **47**, 558 (1993).
- [30] J. M. Soler, E. Artacho, J. D. Gale, A. García, J. Junquera, P. Ordejón, and D. Sánchez-Portal, The SIESTA method for *ab initio* order- N materials simulation, *J. Phys.: Condens. Matter* **14**, 2745 (2002).
- [31] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. D. Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougousis, A. Kokalj, M. Lazzeri, L. Martin-Samos *et al.*, QUANTUM ESPRESSO: A modular and open-source software project for quantum simulations of materials, *J. Phys.: Condens. Matter* **21**, 395502 (2009).
- [32] H. Ebert, D. Ködderitzsch, and J. Minár, Calculating condensed matter properties using the KKR-greens function method—recent developments and applications, *Rep. Prog. Phys.* **74**, 096501 (2011).
- [33] H. Ebert, The SPRKKR code, version 7.7 (2017)
- [34] R. F. L. Evans, W. J. Fan, P. Chureemart, T. A. Ostler, M. O. A. Ellis, and R. W. Chantrell, Atomistic spin model simulations of magnetic nanomaterials, *J. Phys.: Condens. Matter* **26**, 103202 (2014).
- [35] B. Skubic, J. Hellsvik, L. Nordström, and O. Eriksson, A method for atomistic spindynamics simulations: Implementation and examples, *J. Phys.: Condens. Matter* **20**, 315203 (2008).
- [36] G. P. Müller, M. Hoffmann, C. Dißelkamp, D. Schürhoff, S. Mavros, M. Sallermann, N. S. Kiselev, H. Jónsson, and S. Blügel, Spirit: Multifunctional framework for atomistic spin simulations, *Phys. Rev. B* **99**, 224414 (2019).
- [37] M. J. Donahue and D. G. Porter, *Oommfuser's guide version 1.0*. (National Institute of Standards and Technology, Gaithersburg, MD, 1999).
- [38] A. Vansteenkiste, J. Leliaert, M. Dvornik, M. Helsen, F. Garcia-Sanchez, and B. Van Waeyenberge, The design and verification of MuMax₃, *AIP Adv.* **4**, 107133 (2014).
- [39] S. Lepadatu, Boris computational spintronics: High performance multi-mesh magnetic and spin transport modeling software, *J. Appl. Phys.* **128**, 243902 (2020).
- [40] W. Scholz, J. Fidler, T. Schrefl, D. Suess, R. Dittrich, H. Forster, and V. Tsiantos, Scalable parallel micromagnetic solvers for magnetic nanostructures, *Comput. Mater. Sci.* **28**, 366 (2003).
- [41] P. Wohlhüter, M. Bryan, P. Warnicke, S. Gliga, S. Stevenson, G. Heldt, L. Saharan, A. Suszka, C. Moutafis, R. Chopdekar, J. Raabe, T. Thomson, G. Hrkac, and L. Heyderman, Nanoscale switch for vortex polarization mediated by bloch core formation in magnetic hybrid systems, *Nat. Commun.* **6**, 7836 (2015).
- [42] R. Moriya, L. Thomas, M. Hayashi, Y. B. Bazaliy, C. Rettner, and S. S. P. Parkin, Probing vortex-core dynamics using current-induced resonant excitation of a trapped domain wall, *Nat. Phys.* **4**, 368 (2008).
- [43] L. D. Landau and E. Lifshitz, On the theory of the dispersion of magnetic permeability in ferromagnetic bodies, *Phys. Z. Sowjetun.* **8**, 153 (1935).
- [44] T. Gilbert, A phenomenological theory of damping in ferromagnetic materials, *IEEE Trans. Magn.* **40**, 3443 (2004).
- [45] L. Szunyogh, L. Udvardi, J. Jackson, U. Nowak, and R. Chantrell, Atomistic spin model based on a spin-cluster expansion technique: Application to the IrMn_3/Co interface, *Phys. Rev. B* **83**, 024401 (2011).
- [46] T. A. Ostler, J. Barker, R. F. Evans, R. W. Chantrell, U. Atxitia, O. Chubykalo-Fesenko, S. El Moussaoui, L. Le Guyader, E. Mengotti, L. J. Heyderman, F. Nolting, A. Tsukamoto, A. Itoh, D. Afanasiev, B. A. Ivanov, A. M. Kalashnikova, K. Vahaplar, J. Mentink, A. Kirilyuk, T. Rasing *et al.*, Ultrafast heating as a sufficient stimulus for magnetization reversal in a ferrimagnet, *Nat. Commun.* **3**, 666 (2012).
- [47] I. Radu, K. Vahaplar, C. Stamm, T. Kachel, N. Pontius, H. A. Dürr, T. A. Ostler, J. Barker, R. F. L. Evans, R. W. Chantrell, A. Tsukamoto, A. Itoh, A. Kirilyuk, T. Rasing, and A. V. Kimel, Transient ferromagnetic-like state mediating ultrafast reversal of antiferromagnetically coupled spins, *Nature (Lond)* **472**, 205 (2011).
- [48] P. Asselin, R. F. L. Evans, J. Barker, R. W. Chantrell, R. Yanes, O. Chubykalo-Fesenko, D. Hinzke, and U. Nowak, Constrained monte carlo method and calculation of the temperature dependence of magnetic anisotropy, *Phys. Rev. B* **82**, 054415 (2010).
- [49] J. Barker, R. F. L. Evans, R. W. Chantrell, D. Hinzke, and U. Nowak, Atomistic spin model simulation of magnetic reversal modes near the curie point, *Appl. Phys. Lett.* **97**, 192504 (2010).

- [50] M. Strungaru, S. Ruta, R. F. L. Evans, and R. W. Chantrell, Model of Magnetic Damping and Anisotropy at Elevated Temperatures: Application to Granular FePt Films, *Phys. Rev. Appl.* **14**, 014077 (2020).
- [51] D. A. Garanin, Fokker-planck and Landau-Lifshitz-Bloch equations for classical ferromagnets, *Phys. Rev. B* **55**, 3050 (1997).
- [52] U. Atxitia, P. Nieves, and O. Chubykalo-Fesenko, Landau-Lifshitz-Bloch equation for ferrimagnetic materials, *Phys. Rev. B* **86**, 104414 (2012).
- [53] N. Kazantseva, D. Hinzke, U. Nowak, R. W. Chantrell, U. Atxitia, and O. Chubykalo-Fesenko, Towards multiscale modeling of magnetic materials: Simulations of FePt, *Phys. Rev. B* **77**, 184428 (2008).
- [54] T. A. Ostler, M. O. A. Ellis, D. Hinzke, and U. Nowak, Temperature-dependent ferromagnetic resonance via the Landau-Lifshitz-Bloch equation: Application to FePt, *Phys. Rev. B* **90**, 094402 (2014).
- [55] D. Hinzke, U. Atxitia, K. Carva, P. Nieves, O. Chubykalo-Fesenko, P. M. Oppeneer, and U. Nowak, Multiscale modeling of ultrafast element-specific magnetization dynamics of ferromagnetic alloys, *Phys. Rev. B* **92**, 054412 (2015).
- [56] L. Rózsa, U. Atxitia, and U. Nowak, Temperature scaling of the dzyaloshinsky-moriya interaction in the spin wave spectrum, *Phys. Rev. B* **96**, 094436 (2017).
- [57] U. Atxitia, D. Hinzke, O. Chubykalo-Fesenko, U. Nowak, H. Kachkachi, O. N. Mryasov, R. F. Evans, and R. W. Chantrell, Multiscale modeling of magnetic materials: Temperature dependence of the exchange stiffness, *Phys. Rev. B* **82**, 134440 (2010).
- [58] Z. Y. Chen, Z. R. Yan, M. H. Qin, and J.-M. Liu, Landau-Lifshitz-Bloch equation for domain wall motion in antiferromagnets, *Phys. Rev. B* **99**, 214436 (2019).
- [59] F. Jakobs and U. Atxitia, Exchange-enhancement of the ultrafast magnetic order dynamics in antiferromagnets, *arXiv:2206.05783* (2022).
- [60] S. Ruta (private communication, 2022).
- [61] U. Nowak, Classical Spin Models, *Handbook of Magnetism and Advanced Magnetic Materials* (John Wiley & Sons, Ltd, 2007).
- [62] O. K. Andersen, Linear methods in band theory, *Phys. Rev. B* **12**, 3060 (1975).
- [63] A. B. Shick, S. Khmelevskiy, O. N. Mryasov, J. Wunderlich, and T. Jungwirth, Spin-orbit coupling induced anisotropy effects in bimetallic antiferromagnets: A route towards antiferromagnetic spintronics, *Phys. Rev. B* **81**, 212409 (2010).
- [64] H. Callen and E. Callen, The present status of the temperature dependence of magnetocrystalline anisotropy, and the $1/(1+T)$ power law, *J. Phys. Chem. Solids* **27**, 1271 (1966).
- [65] L. Ozyuzer, A. E. Koshelev, C. Kurter, N. Gopalsami, Q. Li, M. Tachiki, K. Kadowaki, T. Yamamoto, H. Minami, H. Yamaguchi, T. Tachiki, K. E. Gray, W.-K. Kwok, and U. Welp, Emission of coherent THz radiation from superconductors, *Science* **318**, 1291 (2007).
- [66] H.-W. Hübers, Towards THz integrated photonics, *Nat. Photon.* **4**, 503 (2010).
- [67] E. A. Nanni, W. R. Huang, K.-H. Hong, K. Ravi, A. Fallahi, G. Moriena, R. J. Dwayne Miller, and F. X. Kärtner, Terahertz-driven linear electron acceleration, *Nat. Commun.* **6**, 8486 (2015).
- [68] N. Bhattacharjee, A. A. Sapozhnik, S. Y. Bodnar, V. Y. Grigorev, S. Y. Agustsson, J. Cao, D. Dominko, M. Obergfell, O. Gomonay, J. Sinova, M. Kläui, H.-J. Elmers, M. Jourdan, and J. Demsar, Retraction: Néel Spin-Orbit Torque Driven Antiferromagnetic Resonance in Mn_2Au Probed by Time-Domain THz Spectroscopy [Phys. Rev. Lett. **120**, 237201 (2018)], *Phys. Rev. Lett.* **124**, 039901(E) (2020).
- [69] U. Atxitia, O. Chubykalo-Fesenko, N. Kazantseva, D. Hinzke, U. Nowak, and R. W. Chantrell, Micromagnetic modeling of laser-induced magnetization dynamics using the Landau-Lifshitz-Bloch equation, *Appl. Phys. Lett.* **91**, 232507 (2007).
- [70] C. Vogler, C. Abert, F. Bruckner, and D. Suess, Landau-Lifshitz-Bloch equation for exchange-coupled grains, *Phys. Rev. B* **90**, 214431 (2014).
- [71] C. Vogler, C. Abert, F. Bruckner, and D. Suess, Stochastic ferrimagnetic Landau-Lifshitz-Bloch equation for finite magnetic structures, *Phys. Rev. B* **100**, 054401 (2019).
- [72] U. Atxitia, D. Hinzke, and U. Nowak, Fundamentals and applications of the Landau-Lifshitz-Bloch equation, *J. Phys. D* **50**, 033003 (2017).
- [73] T. A. Ostler, R. F. L. Evans, R. W. Chantrell, U. Atxitia, O. Chubykalo-Fesenko, I. Radu, R. Abrudan, F. Radu, A. Tsukamoto, A. Itoh, A. Kirilyuk, T. Rasing, and A. Kimel, Crystallographically amorphous ferrimagnetic alloys: Comparing a localized atomistic spin model with experiments, *Phys. Rev. B* **84**, 024407 (2011).
- [74] S. Selzer, L. Salemi, A. Deák, E. Simon, L. Szunyogh, P. M. Oppeneer, and U. Nowak, Current-induced switching of antiferromagnetic order in Mn_2Au from first principles, *Phys. Rev. B* **105**, 174416 (2022).
- [75] P. E. Roy, R. M. Otxoa, and J. Wunderlich, Robust picosecond writing of a layered antiferromagnet by staggered spin-orbit fields, *Phys. Rev. B* **94**, 014439 (2016).
- [76] J. Chen, D. Tzou, and J. Beraun, A semiclassical two-temperature model for ultrafast laser heating, *Int. J. Heat Mass Transf.* **49**, 307 (2006).
- [77] M. Kaganov, I. Lifshits, and L. Tanatarov, Relaxation between electrons and the crystalline lattice, *Sov. Phys. JETP* **31** (1957).
- [78] D. A. Allwood, G. Xiong, C. C. Faulkner, D. Atkinson, D. Petit, and R. P. Cowburn, Magnetic domain-wall logic, *Science* **309**, 1688 (2005).
- [79] S. S. P. Parkin, M. Hayashi, and L. Thomas, Magnetic domain-wall racetrack memory, *Science* **320**, 190 (2008).
- [80] D.-S. Han, S.-K. Kim, J.-Y. Lee, S. J. Hermsdoerfer, H. Schultheiss, B. Leven, and B. Hillebrands, Magnetic domain-wall motion by propagating spin waves, *Appl. Phys. Lett.* **94**, 112502 (2009).
- [81] J.-S. Kim, M. Stärk, M. Kläui, J. Yoon, C.-Y. You, L. Lopez-Diaz, and E. Martinez, Interaction between propagating spin waves and domain walls on a ferromagnetic nanowire, *Phys. Rev. B* **85**, 174428 (2012).
- [82] D. Hinzke and U. Nowak, Domain Wall Motion by the Magnonic Spin Seebeck Effect, *Phys. Rev. Lett.* **107**, 027205 (2011).
- [83] C. Schieback, D. Hinzke, M. Kläui, U. Nowak, and P. Nielaba, Temperature dependence of the current-induced domain wall motion from a modified Landau-Lifshitz-Bloch equation, *Phys. Rev. B* **80**, 214403 (2009).
- [84] K. M. D. Hals, Y. Tserkovnyak, and A. Brataas, Phenomenology of Current-Induced Dynamics in Antiferromagnets, *Phys. Rev. Lett.* **106**, 107206 (2011).

- [85] N. L. Schryer and L. R. Walker, The motion of 180° domain walls in uniform dc magnetic fields, *J. Appl. Phys.* **45**, 5406 (1974).
- [86] J. Shibata, G. Tatara, and H. Kohno, A brief review of field- and current-driven domain-wall motion, *J. Phys. D* **44**, 384004 (2011).
- [87] W. Jiang, P. Upadhyaya, Y. Fan, J. Zhao, M. Wang, L.-T. Chang, M. Lang, K. L. Wong, M. Lewis, Y.-T. Lin, J. Tang, S. Cherepov, X. Zhou, Y. Tserkovnyak, R. N. Schwartz, and K. L. Wang, Direct Imaging of Thermally Driven Domain Wall Motion in Magnetic Insulators, *Phys. Rev. Lett.* **110**, 177202 (2013).
- [88] Y. A. Shokr, O. Sandig, M. Erkovan, B. Zhang, M. Bernien, A. A. Ünal, F. Kronast, U. Parlak, J. Vogel, and W. Kuch, Steering of magnetic domain walls by single ultrashort laser pulses, *Phys. Rev. B* **99**, 214404 (2019).
- [89] S. Selzer, U. Atxitia, U. Ritzmann, D. Hinzke, and U. Nowak, Inertia-Free Thermally Driven Domain-Wall Motion in Antiferromagnets, *Phys. Rev. Lett.* **117**, 107201 (2016).
- [90] F. Schlickeiser, U. Ritzmann, D. Hinzke, and U. Nowak, Role of Entropy in Domain Wall Motion in Thermal Gradients, *Phys. Rev. Lett.* **113**, 097201 (2014).
- [91] O. Gomonay, T. Jungwirth, and J. Sinova, High Antiferromagnetic Domain Wall Velocity Induced by Néel Spin-Orbit Torques, *Phys. Rev. Lett.* **117**, 017202 (2016).
- [92] R. F. L. Evans, L. Rózsa, S. Jenkins, and U. Atxitia, Temperature scaling of two-ion anisotropy in pure and mixed anisotropy systems, *Phys. Rev. B* **102**, 020412(R) (2020).
- [93] Q. Gong, M. Yi, R. F. L. Evans, B.-X. Xu, and O. Gutflisch, Calculating temperature-dependent properties of $\text{Nd}_2\text{Fe}_{14}\text{B}$ permanent magnets by atomistic spin model simulations, *Phys. Rev. B* **99**, 214409 (2019).